



---

UL 444

**STANDARD FOR SAFETY**

Communications Cables

UL Standard for Safety for Communications Cables, UL 444

Fifth Edition, Dated January 20, 2017

***Summary of Topics***

***This new edition of ANSI/UL 444 is being issued to incorporate multiple substantive and editorial changes.***

***As noted in the Commitment for Amendments statement located on the back side of the title page, UL and CSA are committed to updating this harmonized standard jointly.***

The new and revised requirements are substantially in accordance with Proposal(s) on this subject dated June 3, 2016.

All rights reserved. No part of this publication may be reproduced, stored in a retrieval system, or transmitted in any form by any means, electronic, mechanical photocopying, recording, or otherwise without prior permission of UL.

UL provides this Standard "as is" without warranty of any kind, either expressed or implied, including but not limited to, the implied warranties of merchantability or fitness for any purpose.

In no event will UL be liable for any special, incidental, consequential, indirect or similar damages, including loss of profits, lost savings, loss of data, or any other damages arising out of the use of or the inability to use this Standard, even if UL or an authorized UL representative has been advised of the possibility of such damage. In no event shall UL's liability for any damage ever exceed the price paid for this Standard, regardless of the form of the claim.

Users of the electronic versions of UL's Standards for Safety agree to defend, indemnify, and hold UL harmless from and against any loss, expense, liability, damage, claim, or judgment (including reasonable attorney's fees) resulting from any error or deviation introduced while purchaser is storing an electronic Standard on the purchaser's computer system.



CSA Group  
CSA C22.2 No. 214-17  
Eighth Edition



Underwriters Laboratories Inc.  
UL 444  
Fifth Edition

## Communications Cables

January 20, 2017



ANSI/UL 444-2017

## **Commitment for Amendments**

This standard is issued jointly by the Canadian Standards Association (operating as “CSA Group”) and Underwriters Laboratories Inc. (UL). Comments or proposals for revisions on any part of the standard may be submitted to CSA Group or UL at any time. Revisions to this standard will be made only after processing according to the standards development procedures of CSA Group and UL. CSA Group and UL will issue revisions to this standard by means of a new edition or revised or additional pages bearing their date of issue.

---

## **ISBN 978-1-4883-0400-2 © 2017 CSA Group**

All rights reserved. No part of this publication may be reproduced in any form whatsoever without the prior permission of the publisher.

This Standard is subject to review five years from the date of publication, and suggestions for its improvement will be referred to the appropriate committee. To submit a proposal for change, please send the following information to [inquires@csagroup.org](mailto:inquires@csagroup.org) and include “Proposal for change” in the subject line: Standard designation (number); relevant clause, table, and/or figure number; wording of the proposed change; and rationale for the change.

To purchase CSA Group Standards and related publications, visit CSA Group’s Online Store at [shop.csa.ca](http://shop.csa.ca) or call toll-free 1-800-463-6727 or 416-747-4044.

---

## **Copyright © 2017 Underwriters Laboratories Inc.**

UL’s Standards for Safety are copyrighted by UL. Neither a printed nor electronic copy of a Standard should be altered in any way. All of UL’s Standards and all copyrights, ownerships, and rights regarding those Standards shall remain the sole and exclusive property of UL.

This ANSI/UL Standard for Safety consists of the Fifth edition.

The most recent designation of ANSI/UL 444 as an American National Standard (ANSI) occurred on January 20, 2017. ANSI approval for a standard does not include the Cover Page, Transmittal Pages, Title Page (front and back), or the Preface.

The Department of Defense (DoD) has adopted UL 444 on June 12, 1987. The publication of revised pages or a new edition of this Standard will not invalidate the DoD adoption.

Comments or proposals for revisions on any part of the Standard may be submitted to UL at any time. Proposals should be submitted via a Proposal Request in UL’s On-Line Collaborative Standards Development System (CSDS) at <https://csds.ul.com>.

To purchase UL Standards, visit Comm 2000 at <http://www.comm-2000.com/HowToOrder.aspx> or call toll-free 1-888-853-3503.

---

## CONTENTS

<b>Preface</b> .....	5
<b>Communications Cables</b>	
1 Scope .....	6
2 Reference publications .....	6
3 Definitions .....	8
4 General Requirements .....	9
5 Construction .....	9
5.1 Conductors .....	9
5.2 Insulation .....	10
5.3 Optical fibre members .....	11
5.4 Core assembly .....	11
5.5 Defective pairs .....	12
5.6 Spare pairs .....	12
5.7 Core binders .....	13
5.8 Core wrap .....	13
5.9 Shields .....	13
5.10 Jackets .....	13
5.11 Metallic covering .....	14
5.12 Metallic messenger .....	14
6 Manufacturing and Production Tests .....	14
6.1 Spark test after insulating .....	14
6.2 Continuity .....	15
6.3 Dielectric strength .....	15
7 Capability Tests .....	16
7.1 Corrosion resistance of uncoated copper conductors .....	16
7.2 Crush resistance of insulation .....	17
7.3 Insulation unaged and heat-aged requirements .....	18
7.4 Insulation shrinkback .....	19
7.5 Insulation cold bend .....	19
7.6 AC leakage current through overall jacket .....	19
7.7 Durability of printing .....	20
7.8 Unaged and heat-aged requirements of jacket .....	20
7.9 Flexibility (PVDF jackets rated 125°C only) .....	21
7.10 Cable cold bend .....	21
7.11 Jacket peel test .....	22
7.12 Weatherometer test for Type CMX Cable .....	23
7.13 Cold impact of outdoor Type CMX cable .....	23
7.14 Flame and smoke requirements .....	24
7.15 Measuring thickness of insulation and rounding off the results .....	25
7.16 Conductor resistance .....	26
7.17 Conductor diameter or cross-sectional area .....	26
7.18 Compressive loading test for Type CMUC .....	27
7.19 Heat shock test for cross-connect wire .....	27
7.20 Deformation test for cross-connect wire .....	28
7.21 Dielectric tests for cross-connect wire .....	28
7.22 Sunlight resistant test .....	29
7.23 Circuit integrity test for cable marked "-CI" .....	29
7.24 Cable heating test for cables marked "-LP" (XX) .....	29

8	Marking of Cables .....	30
8.1	General .....	30
8.2	Type of marking .....	30
8.3	Required marking .....	30
8.4	Optional marking .....	32
8.5	Intervals .....	33
9	Marking on Tag, Reel, or Carton .....	33
9.1	General requirements .....	33
9.2	Other marking .....	34
10	Date of Manufacture .....	34

## **TABLES**

### **ANNEX A Electrical codes for wire types**

### **ANNEX B Guidelines for sample selection for flame and smoke test requirements**

### **ANNEX C Cable substitutions**

## Preface

This is the common CSA and UL standard for communications cables. It is the eighth edition of CSA C22.2 No. 214 and the fifth edition of UL 444. This edition of CSA C22.2 No. 214 supersedes the previous editions published in 2008, 2002, 1994, 1990, 1988, 1986, and 1984. This UL edition supersedes the previous editions published in 2008, 2002, 1994 and 1990.

This common Standard was prepared by the Canadian Standards Association and Underwriters Laboratories Inc. The efforts of the UL 444/CSA 214 Harmonization Committee are greatly appreciated.

This Standard is considered suitable for use for conformity assessment within the stated scope of the Standard.

This Standard was reviewed by the CSA Subcommittee on Communication Cable, under the jurisdiction of the Technical Committee on Wiring Products and the Strategic Steering Committee on Requirements for Electrical Safety, and has been formally approved by the Technical Committee.

This standard has been approved by the American National Standards Institute (ANSI) as an American National Standard.

### Application of Standard

Where reference is made to a specific number of samples to be tested, the specified number is considered a minimum quantity.

*Note: Although the intended primary application of this Standard is stated in its Scope, it is important to note that it remains the responsibility of the users of the standard to judge its suitability for their particular purpose.*

### Level of Harmonization

This standard uses an IEC format, but is not based on, nor is it to be considered equivalent to, an IEC standard. This standard is published as an identical standard. An identical standard is a standard that is the same in technical content except for conflicts in codes and governmental regulations. Presentation is word for word except for editorial changes.

### Interpretations

The interpretation by the standards development organization of an identical or equivalent standard is based on the literal text to determine compliance with the standard in accordance with the procedural rules of the standards development organization. If more than one interpretation of the literal text has been identified, a revision is to be proposed as soon as possible to each of the standards development organizations to more accurately reflect the intent.

## Communications Cables

### 1 Scope

1.1 This standard applies to 60 – 250°C single- or multiple-conductor jacketed or unjacketed, integral or nonintegral cables and single or multiple coaxial cables for telephone and other communication circuits such as voice, data, and audio for on-premise customer systems. These cables may contain one or more optical fibre members. For the purpose of this standard, a coaxial cable or coaxial member conductor is a single conductor with a shield. For the purpose of this standard, a single- or multiple-conductor unjacketed cable is a cross-connect wire.

1.2 This standard applies to communications cables that are intended primarily for installation in accordance with Section 60 of the *Canadian Electrical Code Part I*, and Article 800 of the *National Electrical Code (NEC)*, ANSI/NFPA 70. They are rated for 300 V applications, but are not so marked.

**Note:** See Annex A for a complete list of wire types covered by this Standard and the specific electrical codes for which they are intended.

1.3 This standard does not apply to communications cords.

1.4 In Canada, the Type “-CI” circuit integrity markings are not recognized by the Canadian Electrical Code, Part I.

In the US, Type CMH is not recognized in the NEC.

1.5 If a value for measurement is followed by a value in other units in parenthesis, the second value may be only approximate. The first stated value is the requirement.

### 2 Reference publications

Any undated reference to a code or standard appearing in the requirements of this standard shall be interpreted as referring to the latest edition of that code or standard.

#### CSA Group

C22.1–15

*Canadian Electrical Code, Part I*

CAN/CSA-C22.2 No. 0–10

*General Requirements – Canadian Electrical Code, Part II*

CSA C22.2 No. 2556–15

*Wire and Cable Test Methods*

#### UL (Underwriters Laboratories)

UL 1581

*Reference Standard for Electrical Wires, Cables, and Flexible Cords*

UL 1666

*Test for Flame Propagation Height of Electrical and Optical-Fiber Cables Installed Vertically in Shafts*



UL 1685

*Vertical-Tray Fire-Propagation and Smoke-Release Test for Electrical and Optical-Fiber Cables*

UL 2196

*Tests for Fire Resistive Cables*

UL 2556

*Wire and Cable Test Methods*

**ANSI (American National Standards Institute)**

Z136 Series

*Safe Use of Lasers*

**ANSI/ASTM (American National Standards Institute/American Society for Testing and Materials)**

E230/E230M

*Standard Specification and Temperature-Electromotive Force (emf) Tables for Standardized Thermocouples*

**ANSI/NFPA (American National Standards Institute/National Fire Protection Association)**

NFPA 70

*National Electrical Code*

**ASTM (American Society for Testing and Materials)**

B33

*Specification for Tinned Soft or Annealed Copper Wire for Electrical Purposes*

B189

*Specification for Lead-Coated and Lead-Alloy-Coated Soft Copper Wire for Electrical Purposes*

B298

*Specification for Silver-Coated Soft or Annealed Copper Wire*

B355

*Specification for Nickel-Coated Soft or Annealed Copper Wire*

B566

*Standard Specification for Copper-Clad Aluminum Wire*

B869

*Specification for Copper-Clad Steel Electrical Conductor for CATV Drop Wire*

D5374

*Test Methods for Forced-Convection Laboratory Ovens for Evaluation of Electrical Insulation*

D5423

*Specification for Forced-Convection Laboratory Ovens for Evaluation of Electrical Insulation*

## NFPA (National Fire Protection Association)

NFPA 262

*Standard Method of Test for Flame Travel and Smoke of Wire and Cables for Use in Air-Handling Spaces*

### 3 Definitions

3.1 The following definitions apply in this standard:

3.2 **BONDED METAL SHIELD** – A covering over the cable core assembly consisting of a metal tape whose outer surface is adhesively bound to a polymeric jacket over it.

3.3 **CAPABILITY TEST** – A test that is conducted periodically on a cable component, or on a completed cable, intended to be proof of adequate construction and processing, and that is repeated for verification.

3.4 **COAXIAL CABLE** – A cable having one or more coaxial members, each consisting of a conductor centred inside one or more outer conductors consisting of metal tubes or shields, separated from the central conductor by a dielectric material.

3.5 **COVERING** – A jacket, sheath, or armour.

3.6 **CROSS-CONNECT WIRE (CABLE)** – A single- or multiple-conductor construction consisting of insulated conductors without an overall jacket.

3.7 **DIELECTRIC** – An insulating (nonconducting) medium.

3.8 **EQUIVALENT GAUGE** – A round conductor AWG number used to designate a flat conductor that has a cross-sectional area equal to that of the round conductor.

3.9 **GROUND PLANE** – A partially encompassing shield provided to reduce stray electrical fields.

3.10 **INTEGRAL COVERING** – A single extruded layer that serves as both insulation and jacket.

3.11 **JACKET** – A continuous nonmetallic outer covering.

3.12 **MANUFACTURING AND PRODUCTION TEST** – A test performed on a length of wire before further processing and/or on a completed cable before shipment.

3.13 **SEMICONDUCTING** – A material whose resistivity at room temperature is in the range of  $10^{-2}$  –  $10^9 \Omega \cdot \text{cm}$ .

3.14 **SHIELD** – A conducting layer consisting of tape, braid, wire, or sheath, or a semiconducting layer.

3.15 **THERMOPLASTIC** – An insulation or jacket material that is capable of being repeatedly softened by heating and hardened by cooling through a temperature range characteristic of the material, and which in its softened state is capable of being shaped through the application of force.

**Note:** *Examples of thermoplastic materials are polyethylene (PE), poly (vinyl chloride) (PVC), nylon, and polyethylene terephthalate (PET).*

3.16 **THERMOSET** – A cross-linked insulating or jacketing compound that does not soften and flow on subsequent heating.

## 4 General Requirements

The requirements of CAN/CSA-C22.2 No. 0, when appropriate, apply to this standard.

## 5 Construction

### 5.1 Conductors

5.1.1 The conductors shall be solid or stranded, annealed, bare, or metal-coated copper. The centre conductor of coaxial cables is also permitted to be a smooth or corrugated copper tube. The centre conductor of CMP, CMR, CMG, CM, CMH, and CMX coaxial cables made of copper-clad steel shall have 21 percent or higher conductivity in accordance with ASTM Standard B869.

5.1.2 The centre conductor of CMP, CMR, CMG, CM, and CMX coaxial cables made of copper-clad aluminum shall be in accordance with ASTM Standard B566.

5.1.3 If the insulation adjacent to the copper conductor is of a material that corrodes unprotected copper in the test described in Clause 7.1, the conductor shall be covered with a coating of tin complying with ASTM Standard B33, of lead or lead-alloy complying with ASTM Standard B189, of nickel complying with ASTM Standard B355, of silver complying with ASTM Standard B298, or of another metal or alloy. Evaluation of the effectiveness of these coatings shall be required. Metal-coating a conductor on which the coating is not required for corrosion protection shall be permitted. When this is done, the 100 percent coverage requirement of the relevant ASTM Standard shall be waived.

The maximum temperature rating of cables relative to the diameter and coating of solid copper conductors or copper conductor strands or the thickness and coating of tubular copper conductors shall not be higher than those shown in Table 1.

5.1.4 For stranded conductors, the length of lay of the strands shall not exceed 20 times the calculated diameter over the assembled conductor for 19 – 6 AWG conductor, or 30 times for 30 – 20 AWG conductor. The direction of lay of the strands may be right- or left-hand.

5.1.5 The conductors shall be continuous when tested in accordance with Clause 6.2.

5.1.6 The size of the copper conductor shall be determined either by means of the resistance shown in Tables 2 and 3, or by means of the dimensions shown in Table 5. In case of dispute, the resistance method shall be the referee method. The size of copper-clad steel or copper-clad aluminum conductor shall be determined by means of the dimensions shown in Table 5. Applications for various AWG sizes and conductor compositions are shown in Table 4.

5.1.7 Resistance shall be determined in accordance with Clause 7.16.

5.1.8 Dimensions shall be determined in accordance with Clause 7.17.

5.1.9 A joint in a solid conductor or in one of the individual wires of a stranded conductor shall be made in a skillful manner, shall be essentially smooth, and shall not have any sharp projections.

A joint in a stranded conductor may be made by:

- a) Separately joining each individual wire; or

- b) Machine brazing or welding of the conductor as a whole.

In either case, the resulting solid section of the stranded conductor shall be not longer than 13 mm (1/2 in), there shall be no sharp points, and the distance between brazes or welds in a single conductor shall not average less than 915 m (3000 ft) in any reel length of insulated single conductor.

A joint made before insulation is applied to a conductor shall not increase the diameter of the solid conductor or individual wire (strand). A joint made after insulating shall not increase the diameter of the solid conductor or individual wire (strand) by more than 20 percent.

The insulation applied to joints after insulating shall be equivalent to that removed (means of insulation such as heat-shrinkable tubing, bonded patch, and molding have been found acceptable, but taping has not) and shall comply with the requirements in this Standard.

5.1.10 Any section of a conductor that includes a factory joint shall have a breaking strength that is not less than 85 percent of the breaking strength of an adjacent section of the conductor without a joint.

5.1.11 "CMX Outdoor" cables shall be smaller in diameter than 6.35 mm (0.25 in).

5.1.12 "CMX Outdoor – CMR" shall also comply with the requirements for CMR cables. These cables may have an overall diameter greater than 6.35 mm (0.25 in).

5.1.13 "CMX Outdoor – CMG" shall also comply with the requirements for CMG cables. These cables may have an overall diameter greater than 6.35 mm (0.25 in).

5.1.14 "CMX Outdoor – CM" shall also comply with the requirements for CM cables. These cables may have an overall diameter greater than 6.35 mm (0.25 in).

## 5.2 Insulation

5.2.1 Each conductor shall be insulated with one or more continuous layers of solid and/or expanded material. The insulation shall be uniform and shall not have any defects (bubbles, open spots, rips, tears, cuts, or foreign material) that are visible without magnification to normal or corrected-to-normal vision. The average thickness of the insulation and the minimum thickness at any point of the insulation are not specified. The average thickness of insulation used, including the average thickness of the tube portion of an air-gap coaxial member, shall be determined by means of an optical device. The method for measuring the thickness of insulation and for rounding off the results shall be as described in Clause 7.15.

5.2.2 The insulation in an air-gap coaxial member shall consist of a solid or foam tube over a solid or foam spacer.

5.2.3 Each conductor, including the centre conductor for a coaxial member, shall meet the dc or ac spark test as described in Clause 6.1 after being insulated and before any subsequent operation. One hundred percent of product shall be tested by the manufacturer at the factory.

5.2.4 The thickness of insulation at any point in a cable with a separable jacket (non-integral construction) shall be sufficient to meet the applicable manufacturing and production tests of Section 6 and the capability tests of Section 7. The thicknesses of the integral insulation (solid) and jacket in 2-, 3-, or 4-conductor flat, parallel cable shall be not less than as indicated in Table 6.

5.2.5 The insulated conductors shall be distinctly identified.

5.2.6 The insulated conductors shall be suitable for indoor use where normal conditions are such that cables may be subjected to maximum operating conditions from 60 – 250°C, inclusive. See Clause 7.3 for temperature rating requirements.

### **5.3 Optical fibre members**

5.3.1 One or more glass fibres that are individually coated and buffered, jacketed either singly in a tight jacket, or in a group in a loose tube, or enclosed in a nonmetallic tape, wrap, or braid that provides complete coverage may be included along with the copper conductors.

5.3.2 An optical fibre member, or group of members, may include one or more metallic or nonmetallic strength members.

5.3.3 The construction of the glass fibre, the coatings, and the fibre jacket is not specified. The construction of nonmetallic tape, wrap, or braid is not specified. The construction of nonmetallic or non-current-carrying metal strength members is not specified.

5.3.4 Non-current-carrying metallic members included in optical fibre member(s) shall be electrically continuous, and shall meet the requirements of Clause 6.2.

### **5.4 Core assembly**

5.4.1 A communications cable shall be essentially round or flat.

5.4.2 Two or more insulated conductors with or without one or more coaxial or optical fibre members shall be assembled to form a cable core. A cable may also consist of one or more coaxial member with or without optical fibre members. A round cable core consisting of 12 or fewer pairs, or 2, 3, or 4 single insulated conductors, may have the pairs or insulated conductors laid straight, but otherwise all conductors, groups of conductors, members, and groups of members shall not be laid straight. In any case, the length of lay is not specified. The direction of lay may be right- or left-hand and may be changed at intervals throughout the length of the cable. The use of fillers is optional. Different conductors and coaxial members may be insulated with different materials if the materials comply with Clause 5.2 on conductor insulation. The conductors in the cable may be of any mixture of sizes and stranding.

5.4.3 When optical fibre member(s) are assembled with other electrical conductors in a common layer, they shall be cabled with the same direction and length of lay as the electrical conductors; otherwise the direction and the length of lay is not specified.

Optical fibre members may include one or more non-current-carrying, electrically conductive members such as a metal strength element or a metal vapour barrier. The construction of these parts is not specified.

## 5.5 Defective pairs

5.5.1 The cable is not acceptable if the applicable factory dielectric strength test described in Clause 6.3 shows any defective pair having a breakdown of the insulation of either conductor to a shield.

5.5.2 A defective pair shall be any pair in which the following discontinuity and/or dielectric faults are revealed in testing by the cable manufacturer at the cable factory:

- a) Discontinuity in either conductor of the pair determined by means of the test described in Clause 6.2; and
- b) One or more of the following dielectric breakdowns of the insulation determined by means of the applicable dielectric strength test described in Clause 6.3:
  - i) Conductor to conductor within the pair;
  - ii) Either conductor of the pair to any conductor outside the pair.

5.5.3 Cables that contain 200 or more pairs may contain acceptable defective pairs in a quantity that shall not exceed 0.5 percent of the number of pairs marked on the tag, reel, or carton for the cable. Both ends of a cable in which there are one or more acceptable defective pairs shall be marked to warn of the presence of the defective pair(s). A notice such as a defective-pair tag shall be attached to each end of a cable in which there are factory-located defects. The notices shall identify the factory counting system (establish a direction for counting multiunits) and shall also identify each of the factory-found acceptable defective pairs according to layer (if pertinent to the counting system), multiunit number, unit colors, and pair color.

## 5.6 Spare pairs

Cables that contain 400 or more pairs may also contain spare pairs to make certain that the number of usable pairs equals or exceeds the number of pairs marked on the tag, reel, or carton. The quantity and position of the spare pairs are not specified. The colors of each spare pair shall be derived from the standard colors and shall be in unique combinations, and it shall not be possible to confuse them with the colors of the regular cable pairs.

## 5.7 Core binders

The core, any group of conductors, or several groups within the core may be bound by a nonmetallic binder. No other details of the core binders are specified.

## 5.8 Core wrap

The core, any group of conductors, or several groups within the core may be enclosed in a nonmetallic core wrap consisting of a serving, wrap, tape, or other construction. A metal shield as described in Clause 5.9.1 may serve as a core wrap. No other details of the core wrap are specified.

## 5.9 Shields

5.9.1 An electromagnetic shield is optional other than as the outer conductor in a coaxial member. One or more shields may be used in a given cable.

5.9.2 Where used, the shield(s) shall be electrically continuous and shall comply with the test requirements of Clause 6.2. To facilitate electrical bonding to ground of the shield(s), a continuous uninsulated, uncoated or metal coated, solid or stranded, copper conductor (drain wire) when used shall be placed in contact with the shield(s). Uncoated copper drain wires shall not be used when aluminum-faced tape is used as a shield.

## 5.10 Jackets

5.10.1 A jacket consisting of a continuous nonmetallic outer covering consisting of a material complying with the requirements of Clauses 5.10.2 – 5.10.8 shall be applied over the cable construction.

5.10.2 The jacket shall be uniform and shall not have any defects (bubbles, open spots, rips, tears, cuts, or foreign material) that are visible without magnification to normal or corrected-to-normal vision.

5.10.3 All cables except those with an overall core wrap as described in Clause 5.8 or an overall bonded or unbonded metal shield as described in Clause 5.9 shall comply with the peel test requirements of Clause 7.11.

5.10.4 Minimum point and minimum average jacket thickness shall be in accordance with requirements specified in Table 7 for jacket materials other than fluoropolymers, and Table 8 for fluoropolymer jacket materials. Maximum average thickness requirements shall be determined from the submitted sample.

For reference purposes, measurements shall be made by means of an optical instrument that is calibrated to read to at least 0.001 mm (0.0001 in).

5.10.5 Jackets with thicknesses other than indicated in Tables 7 and 8 are acceptable if the finished cable complies with the requirements of the tests described in this Standard. Evaluation of thinner jackets shall include, but not be limited to, crush, impact, and abrasion tests.

5.10.6 Cables on which a jacket thicker than as indicated in Table 7 or 8 is necessary to enable the cable to comply with any applicable flame or other test described in these requirements shall be made with whatever greater thickness of jacket may be needed for this purpose. In this case, the minimum thickness at any point of the thicker jacket shall be not less than 80 percent of the average thickness of the heavier jacket.

5.10.7 Jackets shall be capable of meeting the unaged and heat-aged requirements in accordance with Clause 7.8.

5.10.8 Tensile strength values of jacket materials, as specified in Tables 9 and 10 shall be determined in accordance with the test, Insulation and Jacket Physical Properties in CSA C22.2 No. 2556 or UL 2556.

5.10.9 A jacket that is damaged to the point that the underlying assembly is exposed or that is opened for the purpose of repairing a conductor shall either be stripped and replaced in its entirety or have a second jacket applied over the first.

### **5.11 Metallic covering**

An electrically continuous metal sheath or braid may be applied over the jacketed cable (see Note to Table 11).

### **5.12 Metallic messenger**

5.12.1 A metallic messenger may be joined to the outermost jacket by the means of a web. The jacket thickness over the messenger and between the messenger and the cable core is not specified, provided that the required jacket thickness over the conductors is not reduced.

## **6 Manufacturing and Production Tests**

### **6.1 Spark test after insulating**

6.1.1 No insulated conductor shall show more than an average of one fault per 915 m (3000 ft) in any reel length of single insulated conductor when spark tested as described in the test, Spark, of CSA C22.2 No. 2556 or UL 2556.

6.1.2 A dc or ac spark tester shall include a voltage source, an electrode, a voltmeter, a system for detecting, counting, and signalling faults, and the necessary electrical connections. The ability of the equipment to comply with the requirements in Clause 6.1.3 shall be certified at least annually by an accredited independent calibration service or its investigated equivalent such as by checking the test potential with an applicable voltmeter whose calibration is traceable to a nationally recognized standard.

6.1.3 The voltage source of a dc or ac spark tester shall maintain the following test voltage under all normal conditions of leakage current:

- a) An essentially sinusoidal rms potential of 1750 V for an ac test;
- b) 2500 V for a dc test. The current output of which the dc power supply is capable shall not exceed 5 mA. Any ripple shall not exceed 1 percent. After a fault, the dc test voltage shall recover to the full test voltage in 5 ms or less, unless 610 mm (2 ft) or less of the product travels through the electrode in the time that it takes for the full voltage recovery;
- c) For conductor gauge sizes 22 – 30 AWG which are to be used in cables without coaxial members, but with foam or foam skin insulation and protected by bonded metal shields, the following spark test voltage may be used:



Conductor size	Test Voltage
22, 23 AWG	1500 V dc or 1050 V ac
24, 25 AWG	1200 V dc or 850 V ac
26 – 30 AWG	1000 V dc or 750 V ac

d) For cables without bonded metal shields, and with foam insulation that is not more than 0.20 mm (0.008 in) in average thickness and does not have a skin, the spark test voltage may be reduced to 1250 V ac or 1750 V dc, provided that the dielectric strength test voltage required by Clause 6.3.5 is met.

## 6.2 Continuity

The metallic component under test shall be connected in series with an ac or dc source of voltage, less than 30 V, and a means of indicating an unbroken circuit (eg, an incandescent lamp, a bell, or a buzzer). Operation of the indicator shall be evidence of continuity of the component under test.

This test is required only on completed cable before shipment, or on master reels before packaging (put-up). Compliance shall be determined in accordance with the test, Continuity, in CSA C22.2 No. 2556 or UL 2556.

## 6.3 Dielectric strength

6.3.1 The dielectric strength requirement shall be chosen based on the construction (see Clauses 6.3.2 – 6.3.5; see Clause 7.21 for cross-connect wire) and shall be tested in one of the following ways by the cable manufacturer at the cable factory (in accordance with the procedure outlined in the test, Dielectric voltage-withstand, in CSA C22.2 No. 2556 or UL 2556):

a) The jacketed cable shall be tested on each master reel before the final rewind operation, or as individual shipping lengths, or after the final rewind operation. A master reel is any reel containing a single length of finished cable that is intended to be cut into shorter lengths for shipping.

b) For cables produced utilizing a manufacturing process consisting of the cabling/pairing of conductors, jacketing, and packaging in one continuous operation, the following process is permitted:

The first packaged length of finished cable from each production run shall be tested. An additional packaged length shall be tested after 50,000 feet, and each 50,000 feet thereafter.

In the event of a dielectric breakdown of the insulation in a given production run, all the packaged lengths in that run shall be subjected to the dielectric withstand test.

c) The assembled cable shall be tested before the overall jacket is applied. In this case, one shipping length from each master reel of the finished cable shall also be tested. If there is a dielectric breakdown of the insulation on any conductor in the finished cable in that length, 100 percent of the finished cable on the master reel from which the length was taken shall be tested.

**Note:** Where an ac voltage is used, the frequency is to be 48 – 62 Hz.

6.3.2 For all cables except those described in Clauses 6.3.3 – 6.3.5, the insulation shall withstand, without breakdown, a voltage of 2.5 kV dc or 1.5 kV ac for a minimum of 2 s, applied between conductors and between conductors and shields (if present).

6.3.3 For cables with bonded metal shields with foam or foam-skin insulation and conductor gauge sizes 22 – 30 AWG, the foam or foam-skin insulation shall withstand for a minimum of 2 s, without breakdown, the following voltages applied between conductors:

Conductor size	Test voltage
22, 23 AWG	1500 V dc or 1050 V ac
24, 25 AWG	1200 V dc or 850 V ac
26 – 30 AWG	1000 V dc or 750 V ac

In addition, the insulation between the conductors and the bonded shield shall withstand, without breakdown, 5.0 kV dc or 3.0 kV ac for a minimum of 2 s.

6.3.4 For coaxial members, the insulation shall withstand, without breakdown, 2.5 kV dc or 1.5 kV ac for 2 s when the test potential is applied between the conductor and the shield, with the shield connected to earth (ground).

6.3.5 For cables without bonded metal shields, and having foam insulation that is not more than 0.20 mm (0.008 in) in average thickness and that does not have a skin, the dielectric strength test voltage shall be 2000 V ac or 2850 V dc applied for at least 2 s.

## 7 Capability Tests

### 7.1 Corrosion resistance of uncoated copper conductors

Uncoated copper conductors shall be removed from specimens of the finished cable and from specimens of insulated conductors aged at the elevated temperature for the length of time indicated in Clause 7.3 that applies to the insulating material on the conductor. A minimum of three unaged specimens and three aged specimens shall be tested. None of the specimens of the uncoated copper shall show any evidence of pitting or of corrosion compounds in a close visual examination without magnification with normal or corrected-to-normal vision. The test procedure shall be performed in accordance with the test, Copper corrosion, in CSA C22.2 No. 2556 or UL 2556.

## 7.2 Crush resistance of insulation

7.2.1 An average force of at least the level indicated in Table 11 shall be necessary to crush the insulation on a conductor taken from the finished cable to the point that the conductor contacts the earthed (grounded) metal of the testing machine. The test shall be made on an insulated solid conductor as described below, with the results qualifying both solid and stranded conductors having the same form of insulation (solid or foamed) of the same material in the same thicknesses.

7.2.2 The following solid insulations shall be considered to have acceptable crushing strength without this test: solid insulations that are at least 0.15 mm (0.006 in) in average thickness and that are shown by test to have a tensile strength (unaged specimens) of at least 13.8 MPa (2000 lbf/in<sup>2</sup>). All foamed insulation shall be tested.

7.2.3 The insulated conductors shall be removed from a sample length of the finished cable having solid conductors and individually straightened with the fingers. Specimens 180 mm (7 in) long shall be cut from the straight insulated conductors. Each of the five specimens shall be tested separately by being crushed twice between two 50 mm (2 in) wide, flat, horizontal steel plates in a compression machine whose jaws close at the rate of  $5.0 \pm 0.5$  mm/min ( $0.20 \pm 0.02$  in/min). The edges of the plate shall not be sharp. The length of a specimen shall be parallel to the 50 mm (2 in) dimension of the plates, 25 mm (1 in) of the specimen shall extend outside of the plates at one end of the specimen, and 100 mm (4 in) of the specimen shall extend outside the plates at the other end of the specimen.

7.2.4 The plates shall be electrically connected together, to the metal of the testing machine, and to earth (ground). The specimens, the apparatus, and the surrounding air shall be in thermal equilibrium with one another at a temperature of  $24 \pm 8^\circ\text{C}$  throughout the test. The machine shall be started and the specimen subjected to the increasing force of the plates moving toward one another until a short circuit occurs (as indicated by a low-voltage indicator such as a buzzer, lamp, or LED) between the conductor in the specimen and one or both of the earthed (grounded) plates. The maximum force exerted on the specimen before the short circuit occurs shall be recorded as the crushing force for that end of the specimen.

7.2.5 After the short circuit occurs, the machine shall be reversed and the plates separated. The specimen shall be turned end for end, rotated  $90^\circ$ , reinserted (from the end opposite the one originally inserted) between the plates, and crushed. The two crushing forces shall be averaged for each specimen. The average of all ten of the crushing forces obtained for the five specimens shall be used as the value to compare with the requirement in Table 11.

### 7.3 Insulation unaged and heat-aged requirements

#### 7.3.1 For cables to be rated 60°C

Specimens of solid single-layered unaged insulation removed from finished insulated conductors shall have a minimum tensile strength of 8.3 MPa (1200 lbf/in<sup>2</sup>) and a minimum elongation of 100 percent when tested in accordance with the test procedures in CSA C22.2 No. 2556 or UL 2556. Specimens of foam and multiple-layered insulation shall be required to comply only with the flexibility test described below. For the crush resistance test of insulation to be waived (see Clause 7.2.2), the minimum tensile strength shall be 13.8 MPa (2000 lbf/in<sup>2</sup>).

For all insulated conductor types, specimens 305 mm (13 in) long shall be placed in a circulating-air oven conforming to ASTM Standard D5423 (Type II ovens) and ASTM Standard D5374 and maintained at a temperature of 100 ±2°C for 7 d or 121 ±2°C for 48 h. A minimum of six specimens shall be tested. Insulations with band-marking inks may have the ink removed before specimens are aged. After removal from the oven, the specimens shall rest for 16 – 96 h in still air at room temperature and then shall be wound tightly, for six close turns, around a mandrel having a diameter no greater than that of the insulated conductor under test. The insulation shall be examined for cracks using a lens having magnification of 5X. The insulated conductor shall then be straightened, one side of the tube of insulation sliced off with a knife or razor-blade, and the conductor removed for examination of the inner surface of the insulation. There shall be no cracks on either the inside or the outside surface of the insulation. In the event of test results that do not comply, an additional minimum of six specimens shall be tested, all of which shall comply with the requirement.

#### 7.3.2 For cables to be rated 75 – 250°C

7.3.2.1 Specimens of solid single-layered insulations removed from finished insulated conductors shall meet the appropriate values of unaged elongation and tensile strength shown in Table 9 when tested in accordance with the test procedures in CSA C22.2 No. 2556 or UL 2556, except that for insulations with band-marking inks the ink may be removed before specimens are aged. For the crush resistance test of insulation to be waived (see Clause 7.2.2), the minimum tensile strength shall be 13.8 MPa (2000 lbf/in<sup>2</sup>).

7.3.2.2 Specimens of solid single-layered insulations except PVDF rated 125°C shall meet the appropriate values of aged retention of elongation and tensile strength shown in Table 10 when tested in accordance with the test procedures in CSA C22.2 No. 2556 or UL 2556.

7.3.2.3 PVDF rated 125°C, foamed, and multi-layered insulations shall meet the requirements of Clause 7.3.2.4.

7.3.2.4 Specimens of PVDF rated 125°C, foamed, or multiple-layered insulations 305 mm (13 in) long shall be placed in a circulating-air oven conforming to ASTM Standard D5423 (Type II ovens) and ASTM Standard D5374 and aged for the appropriate time and temperature shown in Table 10 for the insulation adjacent to the conductor. When the insulation is foamed, the aging shall be as specified for the solid insulation. A minimum of six specimens shall be tested. Insulations with band-marking inks may have the ink removed before specimens are aged. After removal from the oven, the specimens shall rest for 16 – 96 h in still air at room temperature and then shall be wound tightly, for six close turns, around a mandrel having a diameter no greater than that of the insulated conductor under test. The insulation shall be examined for cracks using a lens having magnification of 5X. The insulated conductor shall then be straightened, one side of the tube of insulation sliced off with a knife or razor-blade, and the conductor removed for examination of the inner surface of the insulation. There shall be no cracks on either the inside or the outside surface of the insulation. In the event of test results that do not comply, an additional minimum of six specimens shall be tested, all of which shall comply with the requirement.

## 7.4 Insulation shrinkback

7.4.1 Immediately before testing, 200 mm (8 in) specimens shall be cut from the centre of a 1.5 m (60 in) length of insulated conductor and then reduced to 150 mm (6 in) by trimming each end of the specimen. For a coaxial cable with a skin over the insulation, the skin shall not be removed. The 150 mm (6 in) specimen shall be placed on a felt bed or on a layer of preheated talc in a circulating-air oven conforming to ASTM Standard D5423 (Type II ovens) and ASTM Standard D5374 and held for 1 h at a temperature specified in Clauses 7.4.2 and 7.4.3. At the end of the conditioning period, the specimen shall cool to room temperature. The total shrinkback of the insulation, which is the sum of the shrinkback measured at both ends of the conductor, shall not exceed 9.5 mm (3/8 in). A minimum of three specimens shall be so tested. In the event of test results that do not comply, an additional three specimens shall be tested, all of which shall comply with the requirement.

7.4.2 For cables to be rated 60 – 105°C, the air oven temperature shall be 121 ±2°C. For materials that melt or deform at this temperature, the test shall be conducted at 115 ±2°C.

7.4.3 For cables to be rated 125 – 250°C, the air oven temperature shall be 150 ±2°C.

## 7.5 Insulation cold bend

Testing to be performed in accordance with the procedure outlined in the test, Cold bend, in CSA C22.2 No. 2556 or UL 2556. Specimens of the insulated conductor and a cylindrical mandrel matched to the diameter of the insulated conductor (see Table 12) shall be conditioned at a temperature of -20 +3, -2°C for not less than 4 h. While still at this temperature, the conductor shall be wound five close turns around the mandrel at a rate of 4 – 6 s per turn. The insulation shall show no visible cracks under normal or corrected-to-normal vision without magnification. A minimum of three specimens shall be so tested. In the event of test results that do not comply, an additional minimum of three specimens shall be tested, all of which shall comply with the requirement.

## 7.6 AC leakage current through overall jacket

7.6.1 The rms current flow through the overall jacket on one specimen of the finished cable shall not exceed 10 mA when a 48 – 62 Hz essentially sinusoidal rms potential of 1500 V is applied as described in Clauses 7.6.2 and 7.6.3. The test potential shall be applied between all of the conductors and any shield(s) connected together and an earthed (grounded) metal foil that is in intimate contact with the centre 150 mm (6 in) of the outside surface of a specimen of any convenient length.

7.6.2 The apparatus shall consist of a circuit breaker, current meter, or other means of indicating an rms current of 10 mA flowing in the test circuit. The test potential shall be supplied by a transformer.

7.6.3 The applied rms potential shall be increased from near zero at an essentially uniform rate that results in 1500 V being applied in 30 s. The potential shall be held constant at 1500 V for 60 s and shall then be reduced to near zero at the rate mentioned above. The cable shall not be acceptable if the rms current through the jacket on the single specimen exceeds 10 mA at any time while the test potential is being increased, held, or decreased.

## 7.7 Durability of printing

7.7.1 All cable types with surface-applied markings of ink shall meet the requirements of the test, Durability of ink printing, in CSA C22.2 No. 2556 or UL 2556.

7.7.2 One specimen shall be heated in a forced-air oven at the temperature and for the period specified for the rated product in Clause 7.8. Upon removal from the oven, the specimen shall be allowed to rest at room temperature for a period of 1 h.

7.7.3 The procedure described in the test, Durability of ink printing, in CSA C22.2 No. 2556 or UL 2556 shall be performed on the as-received specimen conditioned at  $23 \pm 5^\circ\text{C}$ .

7.7.4 The printing on both samples shall remain legible.

## 7.8 Unaged and heat-aged requirements of jacket

7.8.1 Specimens of jacket removed from completed cable shall meet the appropriate values shown in Table 9.

7.8.2 For cables to be rated  $60^\circ\text{C}$ , jacket material removed from a length of finished cable shall meet the aging test as follows. After 7 d, at  $100 \pm 2^\circ\text{C}$ , there shall be at least 50 percent retention of the unaged elongation and 75 percent retention of unaged tensile strength when six specimens are tested in accordance with the test procedures in CSA C22.2 No. 2556 or UL 2556, with the following modifications:

- a) Jackets thinner than 0.46 mm (0.018 in) average, 0.36 mm (0.014 in) minimum at any point shall be buffed only to remove imperfections, not natural indentations.
- b) Cables with an overall diameter not greater than 5.1 mm (0.200 in) may have their jackets tested as tubular specimens rather than as die-cut specimens. Tubular specimens shall not be used for larger cables.

7.8.3 For jackets to be rated  $75 - 250^\circ\text{C}$ , a minimum of six specimens shall be aged for the length of time at the temperature shown in Table 10 and tested in accordance with the procedures in CSA C22.2 No. 2556 or UL 2556, with the following modifications:

- a) Jackets thinner than 0.46 mm (0.018 in) average, 0.36 mm (0.014 in) minimum at any point shall be buffed only to remove imperfections, not natural indentations.
- b) Cables with an overall diameter not greater than 5.1 mm (0.200 in) may have their jackets tested as tubular specimens rather than as die-cut specimens. Tubular specimens shall not be used for larger cables.

Minimum retention of elongation and tensile strength requirements in Table 10 shall be used as pass criteria. This shall apply to all jacket materials except PVDF rated  $125^\circ\text{C}$ . For these materials, the flexibility test described in Clause 7.9 shall be used.

7.8.4 For cables to be rated 75 – 105°C, the maximum cable rating shall be that of the insulation, provided that the jacket rating is not greater than 15°C below the cable rating.

7.8.5 For cables to be rated 125 – 250°C, the lowest of the insulation or jacket ratings shall determine the cable rating.

### **7.9 Flexibility (PVDF jackets rated 125°C only)**

7.9.1 Aged specimens of PVDF jackets rated 125°C in place on the cable shall not show any cracks on either the inside or outside surface after specimens are wound onto a cylindrical mandrel of the diameter indicated in Clause 7.9.2. A minimum of three specimens shall be tested. In the event of test results that do not comply, an additional minimum of three specimens shall be tested, all of which shall comply with the requirement.

7.9.2 The specimens that are to be aged shall be conditioned in accordance with CSA C22.2 No. 2556 or UL 2556, for the length of time and at the temperature indicated for the jacket material in Table 10. The conditioning shall be followed by 16 – 96 h of rest in still air at room temperature before the specimens are wound onto a mandrel. The aged specimens shall be wound at room temperature for six complete turns (adjacent turns touching) onto a circular mandrel having a diameter twice that of the diameter over the overall jacket. Each specimen shall be unwound before being examined.

### **7.10 Cable cold bend**

7.10.1 Testing to be performed as per the procedure outlined in the test, Cold bend, in CSA C22.2 No. 2556 or UL 2556. Specimens of finished cable shall be conditioned to a temperature of  $-20 \pm 3$ ,  $-2^\circ\text{C}$  for a period of 4 h and, while still at this temperature, wound three close turns around a cylindrical mandrel having a diameter as shown in Clause 7.10.2. (If the mandrel is metal, it shall be conditioned at the same temperature.) The jacket and shields (if present) shall show no visible cracks when examined under normal or corrected-to-normal vision. After removal of the test sample from the cold chamber, the rate of bending shall be such that the entire cycle of three bends for small cables up to 3.3 cm (1.3 in) diameter is completed in 30 s and for larger cables in 60 s after removal from the cold chamber. As an alternative the test may be performed in the cold chamber. A minimum of three specimens shall be so tested. In the event of test results that do not comply, an additional minimum of three specimens shall be tested, all of which shall comply with the requirement.

7.10.2 The mandrel diameter shall be a multiple (x) of the diameter over the outside of the cable and shall be based on cable construction as follows:

Cable Construction	Mandrel
No shield(s)	8x
Shield(s) other than those over the completed cable core	12x
Any shield (bonded or unbonded) over the completed cable core	15x

## 7.11 Jacket peel test

7.11.1 The overall jacket on a cable not having an overall metal shield or a nonmetallic core wrap shall be capable of being removed (stripped) without any tearing or other damage to the insulation. The jacket shall be peeled from the cable in 30 s or less time by a weight exerting 13.3 N (3 lbf) when specimens of the finished cable are tested as described in Clauses 7.11.2 – 7.11.4. A minimum of three specimens shall be so tested. In the event of test results that do not comply, an additional minimum of three specimens shall be tested, all of which shall comply with the requirement.

7.11.2 Specimens of 1.2 m (4 ft) length shall be cut from a straight sample length of finished cable that is constructed without a core wrap or shield. Both ends of each specimen shall be cut clean and square. The specimens, the apparatus, and the surroundings shall be in thermal equilibrium with one another at a temperature of  $24 \pm 8^\circ\text{C}$  throughout the test.

7.11.3 The jacket on each specimen shall be slit longitudinally. Cables whose outside diameter is at least 12.7 mm (0.5 in) shall have two slits  $180^\circ$  apart, and smaller cables shall have a single slit. Each cut shall be straight and parallel to the longitudinal axis of the cable and shall extend from one end of the cable to the other. At one end of each specimen, the entire jacket (cable that is slit once) or one half of the jacket (cable with two slits) shall be rolled or folded down over itself a distance of about 50 mm (2 in). The cable assembly thus bared shall be secured in a clamp or other support fixture that does not disturb the circular cross section of the assembly. The cable shall hang down below the support with the longitudinal axis of the cable vertical. A rod, pointer, or other indicator that does not touch the cable shall be adjusted to mark the top of the rolled-down or folded-down portion of the jacket.

7.11.4 A weight that exerts 13.3 N (3 lbf) shall be clamped or otherwise attached to the midpoint of the cut end of the rolled-down or folded-down portion of the jacket. After being attached, the weight shall be released to exert its downward pull on the jacket tending to strip more of the jacket from the cable. The time that it takes for the weight to strip 915 mm (36 in) of jacket from the cable, as measured below the indicator, shall be recorded. The cable shall not be acceptable if more time than 30 s is required for 915 mm (36 in) of jacket to be stripped from the cable.



## 7.12 Weatherometer test for Type CMX Cable

The overall jacket on Type CMX cable that is smaller in diameter than 6.35 mm (0.25 in) and is surface- or tape-marked “outdoor” shall be acceptable for exposure to sunlight if the ratio of the average tensile strength and ultimate elongation of five specimens (conditioned for a period of 300 h) of the overall jacket to the average tensile strength and ultimate elongation of five unaged specimens of the overall jacket is 0.85 or more when the jacket is tested as outlined in the test, Insulation and Jacket Materials – Physical properties, weather (sunlight) resistance, in CSA C22.2 No. 2556 or UL 2556 using either the xenon arc or carbon arc method.

## 7.13 Cold impact of outdoor Type CMX cable

7.13.1 After being conditioned for 4 h in circulating air that is precooled to and maintained at a temperature of  $-10 \pm 2^{\circ}\text{C}$ , the jacket and insulation of finished Type CMX cable that is smaller in diameter than 6.35 mm (0.25 in) and is surface-marked or designated by a marker tape as “outdoor” shall not crack when specimens of the complete cable are subjected to the energy of a free-falling flat-faced circular weight that impacts the cable at the point at which the cable is laid on a horizontal steel anvil.

7.13.2 The impact anvil shall consist of a steel plate having a length of 150 mm (6 in), a width of 90 mm (3-1/2 in), and a thickness of 9.5 mm (3/8 in). A steel ridge 2.4 mm (3/32 in) in height and 1.6 mm (1/16 in) in width shall be positioned in the centre of the plate, perpendicular to the length of the plate, and shall be of the same width as the plate. The two upper edges of the ridge shall have a 0.18 mm (0.007 in) radius. See Figure 3. The anvil shall be secured to a concrete floor, the framework of the building, or another solid support.

7.13.3 The impact energy shall be provided by a weight in the form of a circular steel cylinder having a diameter of 25 mm  $\pm 0.1$  mm (1.0 in  $\pm 0.04$  in) and a flat impact face that is perpendicular to the longitudinal axis of the weight and has rounded edges. The weight of 0.113 kg  $\pm 0.006$  kg (0.25 lb  $\pm 0.0132$  lb) shall enable the weight, when dropped from the height indicated in Clause 7.13.8, to supply an energy of 0.34 J  $\pm 0.02$  J (3 in lbf  $\pm 0.18$  in lbf) to the cable.

7.13.4 The impact specimens shall consist of ten separate 380 mm (15 in) sections cut from a straight sample length of the complete finished cable.

7.13.5 The specimens shall be cooled for 4 h in circulating air that is precooled to and maintained at a temperature of  $-10 \pm 2^{\circ}\text{C}$ . The impact weight and the remainder of the test apparatus shall be in thermal equilibrium with the surrounding air in the test room at a temperature of  $24 \pm 8^{\circ}\text{C}$  through the test.

7.13.6 At the conclusion of the 4 h of cooling, the impact weight shall be supported with its lower face horizontal. A vertical line through the centres of gravity of the impact weight and the stationary anvil shall be coincident with a vertical line through the dimensional centre of the lower face of the impact weight and the dimensional centre of the upper face of the stationary anvil. A set of rails or other vertical guide(s) shall constrain the impact weight and keep its lower face horizontal while the weight is falling and after it has struck the cable. The rails or other guide(s) shall not interfere with the free fall of the impact weight. A mechanism shall be provided at the top of the guide(s) for releasing the impact weight to fall freely through a height of 305 mm (12 in) and strike the cable. A means shall also be provided to keep the weight from striking the cable more than once during each drop.

7.13.7 The ten test specimens of the cable shall be individually removed from the cold chamber and tested in succession, each within 15 s of its removal from the chamber. For the first specimen, the impact weight shall be secured several cable diameters above the anvil, and the specimen shall be placed and secured on the anvil with the longitudinal axis of the specimen horizontal, parallel to the longitudinal axis of the steel anvil (perpendicular to the ridge), and in the vertical plane containing the coincident vertical lines mentioned in Clause 7.13.6.

7.13.8 The position of the impact weight shall be adjusted to place the lower face of the weight 305 mm (12 in) above the upper surface of the first specimen of the cable. The impact weight shall be released from this height, shall fall freely in the guide(s), shall strike the specimen once, and shall then immediately be raised to and secured at the 305 mm (12 in) height. Each of the remaining nine specimens shall be tested likewise from this height.

7.13.9 After each specimen has been impacted, and with a minimum of handling, the specimens shall each be unsecured from the anvil and placed on a horizontal surface away from the apparatus, where they are to rest undisturbed for at least 4 h in still air to warm to a room temperature of  $24 \pm 8^\circ\text{C}$  before being examined for inside and outside surface cracks. The specimens shall then be disassembled and examined further for inside and outside surface cracks in the jacket and in any of the insulation. Cracking on the inside surface of the jacket or insulation can be detected as circumferential depressions in the outer surface of a specimen of material other than a fluoropolymer. Circumferential depressions in a fluoropolymer surface are likely to be yield marks (locally stronger points) rather than indicators of cracking. The examinations shall be made without magnification with normal or corrected-to-normal vision.

7.13.10 The cable shall not be acceptable if any of the cracking described in Clause 7.13.9 is visible in the jacket or insulation of more than two of the ten specimens.

#### **7.14 Flame and smoke requirements**

**Note:** *Annex B gives guidelines for sample selection. Annex C gives permitted cable substitutions.*

7.14.1 Type CMP shall comply with the flame-propagation and smoke-density limits stated in Appendix A of NFPA 262.

7.14.2 Type CMR shall comply with the test described in UL 1666.

7.14.3 Type CMG shall comply with the FT4 test described in vertical tray flame test, of CSA C22.2 No. 2556 or UL 2556 or with the FT4/IEEE 1202 type of flame exposure (smoke measurements are not applicable) described in UL 1685. The length of char shall not exceed 1.5 m (60 in).

7.14.4 Type CM and cross-connect wire, shall comply with the UL flame exposure (smoke measurements are not applicable) described in UL 1685. The char height for each specimen shall be less than 244 cm (8 ft) when measured from the bottom of the cable tray.

7.14.5 Types CMX and CMUC shall comply with the VW-1 flame test described in CSA C22.2 No. 2556 or UL 2556. Burning shall cease within 60 s after any application of flame, and not more than 25 percent of the extended indicator shall be burned. No flaming particles shall drop from the specimen.

7.14.6 Type CMH shall comply with the vertical flame/FT1 test described in CSA C22.2 No. 2556 or UL 2556. Burning shall cease within 60 s, and not more than 25 percent of the extended portion of the indicator shall be burned.

### 7.15 Measuring thickness of insulation and rounding off the results

7.15.1 Thickness measurements of insulation having an average thickness or minimum thickness at any point of not more than 0.152 mm (0.006 in), including any skin, shall be made in accordance with the test, Thickness, in CSA C22.2 No. 2556 or UL 2556.

7.15.2 Rounding off to the nearest 0.0001:

- a) A figure in the fourth decimal place shall remain unchanged if
  - i) the figure in the fifth decimal place is 0 – 4 and the figure in the fourth decimal place is odd or even; or
  - ii) if the figure in the fifth decimal place is 5 and the figure in the fourth decimal place is even (0, 2, 4, and so forth).
- b) A figure in the fourth decimal place shall be increased by 1 if
  - i) the figure in the fifth decimal place is 6 – 9 and the figure in the fourth decimal place is odd or even; or
  - ii) the figure in the fifth decimal place is 5 and the figure in the fourth decimal place is odd (1, 3, 5, and so forth).

7.15.3 Rounding off to the nearest 0.001:

- a) A figure in the third decimal place shall remain unchanged if
  - i) the figure in the fourth decimal place is 0 – 4 and the figure in the third decimal place is odd or even; or
  - ii) if the figure in the fourth decimal place is 5 and the figure in the third decimal place is even (0, 2, 4, and so forth).
- b) A figure in the third decimal place shall be increased by 1 if
  - i) the figure in the fourth decimal place is 6 – 9 and the figure in the third decimal place is odd or even; or
  - ii) the figure in the fourth decimal place is 5 and the figure in the third decimal place is odd (1, 3, 5, and so forth).

#### 7.15.4 Rounding off to the nearest 0.01:

- a) A figure in the second decimal place shall remain unchanged if
  - i) the figure in the third decimal place is 0 – 4 and the figure in the second decimal place is odd or even; or
  - ii) if the figure in the third decimal place is 5 and the figure in the second decimal place is even (0, 2, 4, and so forth).
- b) A figure in the second decimal place shall be increased by 1 if
  - i) the figure in the third decimal place is 6 – 9 and the figure in the second decimal place is odd or even; or
  - ii) the figure in the third decimal place is 5 and the figure in the second decimal place is odd (1, 3, 5, and so forth).

### 7.16 Conductor resistance

7.16.1 Resistance measurements shall be made by testing in accordance with the relevant test procedure of the test, DC resistance, in CSA C22.2 No. 2556 or UL 2556.

7.16.2 For temperatures other than 20 and 25°C, temperature factors for adjusting the dc resistance of conductors shall be made according to Table 1 of CSA C22.2 No. 2556 or UL 2556.

7.16.3 The dc resistance of each cabled conductor in a finished cable shall not exceed the value in Table 2 or 3 when multiplied by the appropriate factor Table 13.

### 7.17 Conductor diameter or cross-sectional area

Measurements of the diameter of a solid conductor or of a wire (strand) from a stranded conductor, the cross-sectional area of a stranded conductor, or the cross-sectional area of a tubular conductor shall be made in accordance with the procedure outlined in the test, Conductor diameter, Cross-sectional area by mass (weight) method, or Cross-sectional area by diameter method, in CSA C22.2 No. 2556 or UL 2556.

## 7.18 Compressive loading test for Type CMUC

7.18.1 A minimum of three specimens, each tested separately, shall be placed between parallel steel plates of a compression machine whose jaws close at a rate of  $5.0 \pm 0.5$  mm/min ( $0.2 \pm 0.02$  in/min). The dimensions of the lower plate shall be such that the test specimen is completely supported during the test, but are otherwise not specified. The dimensions of the upper plate shall be such that it completely covers the steel disk it will be brought to bear down on, but are otherwise not specified. Both plates shall be free of sharp edges and burrs. A 0.5 m (1.6 ft) specimen of finished Type CMUC cable that has been hand-folded back on itself to simulate a right-angle turn shall be placed on the lower plate. A 150 mm (6.0 in) square of commercial carpet, consisting of 300 g/m<sup>2</sup> of nylon with 950 g/m<sup>2</sup> of foam backing, shall be placed over the specimen. A steel disk 13 mm (0.5 in) in diameter, 13 mm (0.5 in) thick, shall be placed over the carpet square and centred over the cable fold. The plates of the compression machine shall be brought together such that they bear down on the steel disk with a force of 1.3 kN (290 lbf) for a period of 3s, and then released. The cycle of applying and releasing the compressive force shall then be repeated four more times. After the five compressive load cycles, the specimen cable shall comply with the dielectric strength test described in Clause 7.18.2 as applicable. The test specimens shall not be straightened between the compressive load cycles or before the dielectric strength test. For cable not designed to be folded, this test shall be performed without folding the specimens.

7.18.2 Specimens of nonshielded Type CMUC cable that have been subjected to the compressive loading test described in Clause 7.18.1 shall be immersed in water for 1 h, with between 153 mm (6 in) and 203 mm (8 in) length submerged to either side of the compressed area. The ends of the specimens shall be kept dry, and shall extend a minimum of 33 mm (1.3 in) above the water. The cable shall withstand, without breakdown, the application of a 48 – 62 Hz sinusoidal or nearly sinusoidal rms potential of 1.0 kV between conductors, and between all conductors and the water for 60 s. The applied potential shall be increased from near zero at a uniform or nearly uniform rate that is not less than 100 percent of the potential rating of the wire or cable in 60 s, and is not more than 100 percent in 10 s (the rate of increase is not to exceed 500 V/s in any case).

## 7.19 Heat shock test for cross-connect wire

The test method shall be in accordance with the test, Heat shock, in CSA C22.2 No. 2556 or UL 2556. The insulation shall be aged in a circulating-air oven conforming to ASTM Standard D5423 (Type II ovens) and ASTM Standard D5374 for 1 h at the temperature of  $100 \pm 1.0$ °C ( $212.0 \pm 1.8$ °F) for cables rated 60°C. For cables rated above 60°C, the conditioning temperature shall be as specified in Table 10. Each specimen shall be tightly wound for six complete turns around a mandrel with a diameter of 1.59 mm (0.062 in). A minimum of three specimens for each insulation type shall be tested. The insulation shall not show any cracks on the inside or outside surface. In the event of test results that do not comply, an additional minimum of six specimens shall be tested, all of which shall comply with the requirement.

## 7.20 Deformation test for cross-connect wire

The test method shall be in accordance with the test, Deformation, in CSA C22.2 No. 2556 or UL 2556. The insulation shall be aged in an air oven at  $100.0 \pm 1.0^\circ\text{C}$  ( $212.0 \pm 1.8^\circ\text{F}$ ). Conductor sizes 16 – 20 AWG shall be subjected to a load of 0.40 kgf or 3.92 N (0.88 lbf). Conductor sizes 21 – 30 AWG shall be subjected to a load of 0.25 kgf or 2.45 N (0.55 lbf). The maximum decrease in insulation thickness shall be 50 percent. A minimum of three specimens for each insulation type shall be tested. In the event of test results that do not comply, an additional minimum of six specimens shall be tested, all of which shall comply with the requirement.

## 7.21 Dielectric tests for cross-connect wire

### 7.21.1 Dielectric test before and after aging on a mandrel tested in water

A minimum of three specimens each shall be tested both before and after the specified conditioning. The overall length of the specimen shall be 457 mm (18 in). Samples of finished wire both before and after aging in an air oven for 1 h at a temperature of  $100^\circ\text{C}$  for cable rated  $60^\circ\text{C}$ , and for cables rated above  $60^\circ\text{C}$  at the temperature and for the time indicated in Table 10, shall be placed in a cold chamber for a period of 1 h at a temperature of  $-10^\circ\text{C}$  ( $14^\circ\text{F}$ ). At the end of the conditioning, the specimens shall be wound around a 1.59 mm (0.062 in) mandrel for six complete and close turns with the ends taped in place. The specimens shall then immediately be placed in a water bath at room temperature for a period of not less than 1 h. The specimens shall be subjected to an applied ac potential that is increased from near zero at a uniform or nearly uniform rate that is not less than 100 percent of the potential rating of the wire or cable in 60 s and is not more than 100 percent in 10 s (the rate of increase is not to exceed 500 V/s in any case). This ac potential shall be applied between the conductor and an electrode placed in water until 1500 V (1060 V dc) is attained. The test potential shall be held for a period of 1 min without breakdown. All specimens shall withstand the 1500 V potential for 1 min without breakdown. In the event of test results that do not comply, an additional six specimens shall be tested, all of which shall comply with the requirement.

### 7.21.2 Dielectric test on unaged specimens in water at room temperature

Six metres (20 ft) of 7.6 m (25 ft) coils shall be immersed in a tank of water at room temperature for not less than 12 h. At the end of this period, an ac potential that is increased from near zero at a uniform or nearly uniform rate that is not less than 100 percent of the potential rating of the wire or cable in 60 s, and is not more than 100 percent in 10 s (the rate of increase is not to exceed 500 V/s in any case) shall be applied between the conductor and an electrode placed in water until 1500 V (1060 V dc) is attained. This test potential shall be held for a period of 1 min. Three specimens each shall be tested. All specimens shall withstand the 1500 V potential for 1 min without breakdown. In the event of test results that do not comply, an additional minimum of six specimens shall be tested, all of which shall comply with the requirement.

## 7.22 Sunlight resistant test

Any cable that is marked for sunlight-resistant use as described in Clause 8.3.8 shall be considered acceptable for use in sunlight if the ratio of the average tensile strength and ultimate elongation of five conditioned specimens of the overall jacket to the average tensile strength and ultimate elongation of five unconditioned specimens of the overall jacket is 0.80 or more, when the finished cable is conditioned and tested in accordance with the weather (sunlight) resistance test in CSA C22.2 No. 2556 or UL 2556, using 720 h of carbon-arc exposure, or xenon-arc exposure.

## 7.23 Circuit integrity test for cable marked "-CI"

*(United States only)*

Cable that is marked as specified in Clause 8.4.3 to indicate circuit integrity shall comply with the requirements for cable marked "-CI" in Tests for Fire Resistive Cables, UL 2196.

## 7.24 Cable heating test for cables marked "-LP" (XX)

7.24.1 When tested as described in Clause 7.24.2 and 7.24.3, the temperatures measured on the insulation and jacket of the cables, after being corrected to an ambient of 45°C, shall not exceed the temperature rating of the cable. The temperature shall be determined by measuring the temperature rise at room ambient and then adding 45°C.

7.24.2 The cables shall be arranged in a bundle consisting of 192 cables and electrically connected in series to a power supply capable of providing the rated current marked as part of the LP rating. The inner 37 cables shall be arranged in a hexagonal densest packing structure which represents the worst case thermal dissipation situation. The remaining cables shall be evenly distributed in a random fashion to form a 192-cable bundle. The bundle shall be placed in a 1.83 m ± 5 cm (6 foot ± 2 in) long commercially available non-metallic conduit (Schedule 40) with the minimum diameter needed to install the bundle without putting pressure on the cables. Each end of the conduit shall be filled with insulation.

7.24.3 The temperatures shall be measured on the outer jacket and conductor insulation of the centre cable at the midpoint of the cable. In addition, temperatures shall be measured on the jacket and conductor insulation on the centre cable 0.6 m (2 ft) on each side of centre thermocouple.

7.24.4 Temperatures shall be measured by means of thermocouples that are not larger than 24 AWG (0.21 mm<sup>2</sup>) and not smaller than 30 AWG (0.05 mm<sup>2</sup>). When thermocouples are used in determining temperatures, it is common practice to employ thermocouples consisting of 30 AWG iron and constantan wires with a suitable indicating instrument. This equipment shall be used whenever a referee measurement of temperature is necessary.

7.24.5 The thermocouples and related instruments shall be accurate and calibrated in accordance with standard laboratory practice. The thermocouple wire shall conform to the requirements specified in the Tolerances on Initial Values of EMF versus Temperature tables in ANSI/ASTM E230/E230M.

7.24.6 A thermocouple junction and adjacent thermocouple lead wire shall be securely held in good thermal contact with the surface of the material whose temperature is being measured. In most cases, acceptable thermal contact results from securely taping or cementing the thermocouple in place.

## **8 Marking of Cables**

### **8.1 General**

Markings shall be readily legible and repeated at intervals in accordance with Clause 8.5 throughout the entire cable length. The voltage rating for the cable shall not be marked on or in the cable. Surface marking of cross-connect wire is not required.

### **8.2 Type of marking**

#### **8.2.1 General**

The type of marking shall be as specified in Clause 8.2.2 or 8.2.3, as applicable.

#### **8.2.2 Surface marking**

Surface marking shall be ink, indented, or embossed marking that is printed on the outside surface of the overall jacket.

#### **8.2.3 Printed marker tapes**

Printed marker tapes shall be allowed only as follows:

- a) Directly under a transparent or translucent jacket, provided that it is readily legible through the jacket;
- b) Anywhere in the cable, outside an insulated conductor, and outside a unit assembly, and only for cable whose outermost covering is wire armour, a metal braid, or interlocked armour; or
- c) Where impracticality of a surface marking is demonstrated.

### **8.3 Required marking**

#### **8.3.1 General**

The sequence of items is not specified.



### 8.3.2 AWG size

For cables with all conductors of the same size, only the size (but not the quantity) shall be required. If a coaxial member(s) is present, the size shall be marked.

For cables containing a mixture of AWG sizes, the quantity and size of each shall be required.

Conductors that exceed the maximum resistance requirement in Tables 2 and 3 for a specific AWG size shall be identified as the AWG of the next smaller AWG conductor (next higher AWG number).

The use of marking "AWG" shall be optional.

### 8.3.3 Flame test classification

8.3.3.1 Cables shall be marked as follows:

- a) CMP – for cables meeting CSA FT6 or NFPA 262;
- b) CMR – for cables meeting UL 1666;
- c) CMG – for cables meeting CSA FT4 or FT4/IEEE 1202 type of flame exposure (without smoke measurements) in UL 1685;
- d) CM or cross-connect – for cables meeting UL flame exposure (without smoke measurements) in UL 1685;
- e) CMX or CMUC – for cables meeting the VW-1 test specified in CSA C22.2 No. 2556 or UL 2556
- f) CMH – for cables meeting vertical flame/FT1 test of CSA C22.2 No. 2556 or UL 2556.

8.3.3.2 Cables containing optical fibre member(s) shall be marked with the suffix "-OF" after the type designations in Clause 8.3.3.1.

### 8.3.4 Responsible organization

Markings shall specify the name, trade name, or applicable mark, or file number, as well as manufacturing location identification if the cable is manufactured in more than one location. The manufacturing location identification is the name of the cable manufacturer, that manufacturer's trade name for the cable, or both, or any other distinctive marking by means of which the manufacturing location for the cable can readily be identified.

### 8.3.5 Temperature rating

For cable rated over 60°C, the temperature rating shall be stated as °C or C.

### 8.3.6 Type "CMX Outdoor"

A cable which meets the requirements in 5.1.11, passes the VW-1 flame test in CSA C22.2 No. 2556 or UL 2556, and meets the weatherometer test and the cold impact test described in Clauses 7.12 and 7.13 of this standard may be marked "CMX Outdoor".

Cables meeting the requirements in 5.1.12, pass the VW-1 flame test in CSA C22.2 No. 2556 or UL 2556, and meet the weatherometer test and the cold impact test described in Clauses 7.12 and 7.13 of this standard may be marked "CMX Outdoor-CMR".

Cables meeting the requirements in 5.1.13, pass the VW-1 flame test in CSA C22.2 No. 2556 or UL 2556, and meet the weatherometer test and the cold impact test described in Clauses 7.12 and 7.13 of this standard may be marked "CMX Outdoor-CMG".

Cables meeting the requirements in 5.1.14, pass the VW-1 flame test in CSA C22.2 No. 2556 or UL 2556, and meet the weatherometer test and the cold impact test described in Clauses 7.12 and 7.13 of this standard may be marked "CMX Outdoor-CM".

### 8.3.7 "AUDIO ONLY" cable

Cables, other than coaxial cable, that employs 15 – 6 AWG copper conductors shall be marked with the words "AUDIO ONLY" in addition to other required markings.

**Note:** *Coaxial cable is not required to be marked with the words "AUDIO ONLY".*

### 8.3.8 Sunlight resistant

Cable that complies with the sunlight-resistant test referenced in Clause 7.22 shall be marked with the designation "sun res" or "sunlight resistant".

## 8.4 Optional marking

8.4.1 "Shielded" may be marked on cable containing one or more shields.

8.4.2 The temperature rating of 60°C rated cable may be included if marked in accordance with Clause 8.3.5.

8.4.3 Cable that complies with the requirements in Clause 7.23 may be marked with the suffix "CI". If so marked, the suffix "-CI" shall be added immediately after the cable designation. This marking is not required.

8.4.4 Sequential length marking may be specified.

8.4.5 Cables may be marked with other information, except a voltage rating, if the information does not confuse or mislead. Cables with multiple qualifications, such as additional NEC type(s) or AWM, include voltage ratings among additional markings. The additional multiple markings as a group shall be clearly separated from other markings.

8.4.6 Cables that comply with the cable heating test described in Clause 7.24 may be marked with the suffix LP (XX) where XX shall be 0.5A, 0.6A, 0.7A, 0.8A, 0.9A, or 1.0A to designate the current rating of each conductor in the cable. If so marked, the suffix "LP" shall be added immediately after the cable designation. This marking is optional.

## 8.5 Intervals

8.5.1 Required marking shall appear at intervals throughout the entire cable length as specified in Clauses 8.5.2 and 8.5.3.

8.5.2 All required markings on the outside surface of the overall jacket or on a marker tape visible through the overall jacket shall be repeated at intervals that are not greater than 1 m (40 in).

8.5.3 Where permitted by Clause 8.2.3 (b) or (c), markings on a marker tape not visible through the overall jacket shall be repeated at intervals not greater than 635 mm (25 in).

## 9 Marking on Tag, Reel, or Carton

### 9.1 General requirements

9.1.1 The information specified in Clauses 9.1.2 – 9.1.8 shall be on a tag affixed to each shipping length of cable, its reel or carton, or directly printed on the reel or carton.

9.1.2 All of the information required in Clause 8.3 shall be provided.

9.1.3 The number of conductors or pairs shall be provided.

9.1.4 The date of manufacture by month and year shall be provided. See Section 10 for requirements relating to date marking on the cable.

9.1.5 If the cable is also marked AWM (Appliance Wiring Materials) style, the voltage marking shall be acceptable.

9.1.6 For a cable that contains one or more optical fibres, the following statement, or another statement to the same effect, shall be provided:

"Optical fibre portion(s) of cable are for installation (optical and electrical functions associated) as described in applicable parts of the *Canadian Electrical Code, Part I*, and the *National Electrical Code* (ANSI/NFPA 70). Where optical fibre is installed in a laser system, the system shall comply with the ANSI Z136 laser system safety Standards."

9.1.7 For a cable that contains one or more optical fibre members with any individual optical fibre member or group of such members having a metal or other electrically conductive part, the following wording, or other wording to the same effect, shall be provided:

“Optical fibre portion(s) of cable contain non-current-carrying metal or other electrically conductive parts.”

9.1.8 For a cable, other than a coaxial cable, employing 15 – 6 AWG copper conductors, the following wording shall be provided: “For use in audio applications only.”

## 9.2 Other marking

Other information may be added if it does not confuse or mislead.

## 10 Date of Manufacture

For cable on which the outer surface is a jacket, the date of manufacture by month and year shall be included among the tag, reel, or carton markings described in Clause 9.1 or shall be included among the product markings described in this Standard, where legible on or through the outer surface of the cable.

## TABLES

**Table 1**  
**Maximum temperature rating of cables relative to diameter and coating of the solid copper conductor or of each copper conductor strand or thickness and coating of the tubular copper conductor**  
**(See Clause 5.1.3.)**

Metal coating	Diameter of each strand or of the solid conductor or thickness of the tubular conductor	
	Smaller than 0.38 mm (0.015 in)	At least 0.38 mm (0.015 in)
Uncoated, tin or tin/lead alloy coating	150°C	200°C
Silver coating	200°C	200°C
Nickel coating	over 200°C	over 200°C

**Table 2**  
**Maximum direct current resistance of copper conductors in ohms per km**  
**(See Clauses 5.1.6 and 7.16.3, and 8.3.2.)**

Conductor size (AWG)	Stranded conductor				Solid or tubular conductor			
	Uncoated		Coated		Uncoated		Coated	
	20°C	25°C	20°C	25°C	20°C	25°C	20°C	25°C
30	354	361	371	377	374	384	390	397
29	277	282	288	294	293	299	305	311
28	223	227	232	236	236	240	245	250
27	175	179	182	186	185	189	193	197
26	140	143	145	148	148	151	154	157
25	111	113	115	117	117	119	121	124
24	87.6	89.2	90.9	93.2	93.8	95.8	103	105
23	69.2	70.5	71.9	73.2	73.2	74.5	76.1	77.8
22	55.4	56.4	57.4	58.7	59.1	60.4	65.0	66.3
21	43.6	44.6	45.6	46.3	46.3	47.2	48.2	49.2
20	34.4	35.1	35.8	36.4	36.4	37.1	38.1	38.7
19	27.5	28.4	28.6	29.1	29.1	29.7	30.2	30.8
18	21.9	22.3	22.7	23.1	21.4	21.8	22.2	22.7
17	17.4	17.7	17.9	18.3	16.9	17.2	17.6	17.9
16	13.7	14.0	14.3	14.6	13.5	13.7	14.0	14.3
15	10.8	11.1	11.3	11.5	10.6	10.8	11.1	11.3
14	8.60	8.76	8.96	9.09	8.45	8.61	8.78	8.96
13	6.82	6.96	7.09	7.22	6.69	6.82	6.96	7.09
12	5.41	5.51	5.61	5.71	5.31	5.42	5.53	5.64
11	4.33	4.43	4.49	4.59	4.22	4.30	4.39	4.48
10	3.41	3.48	3.54	3.61	3.34	3.41	3.48	3.55
9	2.705	2.758	2.813	2.868	2.652	2.704	2.730	2.784
8	2.144	2.186	2.230	2.274	2.102	2.143	2.163	2.206
7	1.700	1.734	1.768	1.802	1.667	1.699	1.716	1.749
6	1.348	1.375	1.403	1.430	1.323	1.348	1.361	1.388

**Table 3**  
**Maximum direct current resistance of copper conductors in ohms per 1000 ft**  
**(See Clauses 5.1.6, 7.16.3, and 8.3.2.)**

Conductor size (AWG)	Stranded conductor				Solid or tubular conductor			
	Uncoated		Coated		Uncoated		Coated	
	20°C	25°C	20°C	25°C	20°C	25°C	20°C	25°C
30	108	110	113	115	114	117	119	121
29	84.5	86.1	87.9	89.6	89.3	91.1	92.9	94.7
28	67.9	69.3	70.7	72.0	71.8	73.3	74.7	76.2
27	53.4	54.5	55.6	56.6	56.5	57.6	58.8	59.9
26	42.7	43.6	44.4	45.2	45.1	46.0	46.9	47.8
25	33.7	34.4	35.0	35.7	35.6	36.3	37.0	37.7
24	26.7	27.2	27.7	28.4	28.6	29.2	31.5	32.1
23	21.1	21.5	21.9	22.3	22.3	22.7	23.2	23.7
22	16.9	17.2	17.5	17.9	18.0	18.4	19.8	20.2
21	13.3	13.6	13.9	14.1	14.1	14.4	14.7	15.0
20	10.5	10.7	10.9	11.1	11.1	11.3	11.6	11.8
19	8.39	8.66	8.71	8.87	8.86	9.04	9.21	9.39
18	6.66	6.79	6.92	7.04	6.52	6.65	6.78	6.91
17	5.29	5.40	5.47	5.59	5.15	5.25	5.36	5.47
16	4.19	4.27	4.35	4.44	4.10	4.18	4.26	4.35
15	3.30	3.37	3.44	3.50	3.24	3.30	3.37	3.43
14	2.62	2.67	2.73	2.77	2.57	2.62	2.68	2.72
13	2.08	2.12	2.16	2.20	2.04	2.08	2.12	2.16
12	1.65	1.68	1.71	1.74	1.62	1.65	1.68	1.71
11	1.32	1.35	1.37	1.40	1.29	1.32	1.34	1.37
10	1.04	1.06	1.08	1.10	1.02	1.04	1.06	1.08
9	0.8245	0.8407	0.8574	0.8742	0.8084	0.8242	0.8319	0.8483
8	0.6535	0.6663	0.6795	0.6929	0.6407	0.6532	0.6594	0.6724
7	0.5182	0.5284	0.5389	0.5495	0.5081	0.5181	0.5229	0.5332
6	0.4112	0.4192	0.4276	0.4359	0.4031	0.4110	0.4148	0.4230

**Table 4**  
**Conductor metal and application**  
**(See Clause 5.1.6.)**

Conductor metal	Conductor size (AWG)	Application
Copper	30-16	Multiple-conductor or Coaxial Cable
Copper	30-16	Cross-connect Wire (Cable)
Copper	15-6	Coaxial or Audio Cable
Copper-clad steel or Copper-clad aluminum	30-6	Coaxial Cable only

**Table 5**  
**Minimum diameter for solid conductors and cross-sectional area for tubular or stranded conductors**  
**(See Clause 5.1.6.)**

Conductor size (AWG)	Diameter of solid conductor		Cross-sectional area of tubular or stranded conductor		
	mm	in	mm <sup>2</sup>	cmil	
30	0.251	0.0099	0.0497	98	
29	0.284	0.0112	0.0633	125	
28	0.318	0.0125	0.0790	156	
27	0.358	0.0141	0.100	198	
26	0.384 <sup>a</sup>	0.0151 <sup>a</sup>	0.126	248	
25	0.432 <sup>a</sup>	0.0170 <sup>a</sup>	0.159	314	
24	0.485 <sup>a</sup>	0.0191 <sup>a</sup>	0.201	396	
23	0.546 <sup>a</sup>	0.0215 <sup>a</sup>	0.254	501	
22	0.610 <sup>a</sup>	0.0240 <sup>a</sup>	0.318	627	
21	0.688 <sup>a</sup>	0.0271 <sup>a</sup>	0.404	796	
20	0.772 <sup>a</sup>	0.0304 <sup>a</sup>	0.509	1000	
19	0.866 <sup>a</sup>	0.0341 <sup>a</sup>	0.641	1264	
18	1.013	0.0399	0.807	1588	
17	1.138	0.0448	1.02	2009	
16	1.278	0.0503	1.28	2528	
15	1.435	0.0565	1.62	3195	
14	1.613	0.0635	2.04	4028	
13	1.81	0.0713	2.58	5076	
12	2.03	0.0800	3.24	6399	
11	2.28	0.0898	4.09	8065	
10	2.56	0.1010	5.16	10172	
9	2.87	0.113	6.50	12828	
8	3.22	0.127	8.20	16180	
7	3.63	0.143	10.34	20404	
6	4.06	0.160	13.03	25715	

<sup>a</sup> Minimum acceptable diameter (0.95 x nominal) of a solid conductor of this size.

**Table 6**  
**Thickness of integral insulation (solid) and jacket on 2-, 3- or 4-conductor flat, parallel cable and distance between conductors**  
**(See Clause 5.2.4.)**

Cable types and sizes	Nominal thickness away from tear area(s) (vertical dashed line through web or webs in Figure 1) and outside point P or X (defined in Figure 2)		Minimum thickness at any point before separation measured outside point P or X (defined in Figure 2)		Minimum thickness at any point after separation		Minimum distance between copper conductors	
	A <sup>a</sup> (Information only – not a requirement)		B <sup>a</sup>		C <sup>a</sup>		D <sup>a</sup>	
	in	mm	in	mm	in	mm	in	mm
24 – 8 AWG	0.030	0.76	0.027	0.69	0.013	0.33	0.047	1.19
7 – 6 AWG	0.045	1.14	0.040	1.02	0.027	0.69	0.080	2.03

<sup>a</sup> Dimensions A – D are illustrated in Figure 1.

**Table 7**  
**Thickness<sup>a</sup> of overall jacket (except for fluoropolymers)**  
**(See Clauses 5.10.4 – 5.10.6.)**

Cable core diameter mm (in)	Tensile strength less than 17.24 MPa (2500 psi) mm (in)		Tensile strength at least 17.24 MPa (2500 psi) mm (in)	
	Minimum average thickness	Minimum thickness at any point	Minimum average thickness	Minimum thickness at any point
0.0 – 3.3 (0.00 – 0.13)	0.33 (0.013)	0.25 (0.010)	0.33 (0.013)	0.25 (0.010)
Over 3.3 – 8.89 (0.13 – 0.35)	0.58 (0.023)	0.46 (0.018)	0.33 (0.013)	0.25 (0.010)
Over 8.89 – 10.16 (0.35 – 0.40)	0.69 (0.027)	0.56 (0.022)	0.46 (0.018)	0.36 (0.014)
Over 10.16 – 17.78 (0.40 – 0.70)	0.81 (0.032)	0.66 (0.026)	0.46 (0.018)	0.36 (0.014)
Over 17.78 – 38.10 (0.70 – 1.50)	1.14 (0.045)	0.91 (0.036)	0.76 (0.030)	0.61 (0.024)
Over 38.10 – 63.50 (1.50 – 2.50)	1.52 (0.060)	1.22 (0.048)	1.14 (0.045)	0.91 (0.036)
Over 63.50 – 88.90 (2.50 – 3.50)	1.91 (0.075)	1.52 (0.060)	1.52 (0.060)	1.22 (0.048)

<sup>a</sup> A thicker jacket may be required to enable the cable to comply with one or more tests.

**Note:** For cables that are not round, the equivalent diameter shall be calculated as  $1.1284(TW)^{1/2}$  where



**Table 7 Continued**

Cable core diameter mm (in)	Tensile strength less than 17.24 MPa (2500 psi) mm (in)		Tensile strength at least 17.24 MPa (2500 psi) mm (in)	
	Minimum average thickness	Minimum thickness at any point	Minimum average thickness	Minimum thickness at any point

*T = the thickness of the cable*  
*W = the width of the cable.*

**Table 8**  
**Thickness<sup>a</sup> of overall fluoropolymer jacket**  
**(See Clauses 5.10.4 – 5.10.6.)**

Cable core diameter mm (in)	Minimum average thickness mm (in)	Minimum thickness at any point mm (in)
Over 0.00 – 6.35 (0.00 – 0.25)	0.20 (0.008)	0.15 (0.006)
Over 6.35 – 8.89 (0.25 – 0.35)	0.25 (0.010)	0.20 (0.008)
Over 8.89 – 12.70 (0.35 – 0.50)	0.33 (0.013)	0.25 (0.010)
Over 12.70 – 17.78 (0.50 – 0.70)	0.38 (0.015)	0.30 (0.012)
Over 17.78 – 38.10 (0.70 – 1.50)	0.51 (0.020)	0.41 (0.016)

<sup>a</sup> A thicker jacket may be required to enable the cable to comply with one or more tests.

**Notes:**

1) A jacket that is applied directly over wire serving, wrap, or braid (no intervening wrap or other protective covering) shall not be thinner in average thickness than 0.33 mm (0.013 in) and shall not be thinner at any point than 0.25 mm (0.010 in).

2) For cables that are not round, the equivalent diameter shall be calculated as  $1.1284(TW)^{1/2}$

where

*T = the thickness of the cable*

*W = the width of the cable.*

**Table 9**  
**Minimum unaged properties of insulations and jackets**  
 (See Clauses 5.10.8, 7.3.2.1, and 7.8.1.)

Material	Ultimate elongation percent	Tensile strength	
		MPa	lbf/in <sup>2</sup>
ECTFE ETFE	100	34.5	5000
FEP	200	17.2	2500
FRPE, FRPP	100	8.3	1200
HDPE	300	16.5	2400
LDPE	350	9.7	1400
MFA, PFA	200	17.2	2500
PP	150	20.7	3000
PTFE	175	27.6	4000
PVC	100	13.8	2000
PVDF	100	24.1	3500
SRPVC	100	20.7	3000
TPE	300	9.65	1400
XL	150	10.3	1500
XLPO	150	13.8	2000

**Notes:**

1) All materials shall be tested at 500 ±25 mm/min (20 ±1 in/min) except ECTFE, ETFE, FRPE, FRPP, HDPE, PP, PVDF, and SRPVC. These materials shall be tested at 50 ±5 mm/min (2.0 ±0.2 in/min).

2) An insulation or a jacket of a material other than one of those mentioned in the first column of this table may be used, provided that it has been evaluated to verify acceptability for use in the intended application.

**Table 10**  
**Heat-aged properties of insulation and jackets for ratings 75 – 250°C**  
 (See Clauses 5.10.8, 7.3.2.2, 7.3.2.4, 7.8.3, 7.9.2, 7.19, and 7.21.1.)

Rating (°C)	Jacket or insulation	Time (days)	Temperature (°C)	Min. retention ( percent) of unaged	
				Elongation	Tensile strength
75	FRPE, FRPP	2	100	75	75
	HDPE	2	100	75	75
	LDPE	2	100	75	75
	PP	10	100	70	70
	PVC	10	100	50	85
	SRPVC	7	113	70	70
	XL	7	113	70	70
90	PVC	7	121	50	85
	SRPVC	7	121	70	70
	XL	7	121	70	70
	TPE	7	121	75	75
105	XLPO	7	136	70	85
	PVC	7	136	50	85
	SRPVC	7	136	70	70
	TPE	7	136	75	75
125	PVDF	7	158	Flex test on mandrel	
		or 30	136		
150	ECTFE, ETFE	7	180	75	85 <sup>a</sup>
	PVDF	60	158	50	50
200	FEP	7	232	75	75

Table 10 Continued on Next Page

**Table 10 Continued**

Rating (°C)	Jacket or insulation	Time (days)	Temperature (°C)	Min. retention ( percent) of unaged	
				Elongation	Tensile strength
250	MFA, PFA	4	260	85	85
	PTFE	60	260	85	85
	MFA, PFA	7	287	85	85

<sup>a</sup> Or 34.5 MPa (5000 lb/in<sup>2</sup>) minimum.

**Note:** An insulation or a jacket of a material other than one of those mentioned in the first column of this table may be used, provided that it has been evaluated to verify acceptability for use in the intended application.

**Table 11  
Crushing force for insulations  
(See Clauses 5.11, 7.2.1, and 7.2.5.)**

Source of conductors	Minimum acceptable average force to crush insulated conductor	
	N	lbf
From cables with a bonded metal shield or its evaluated equivalent:		
Conductors from a cable having a bonded metal shield	890	200
From all other cables:		
Conductors from a cable without a metallic sheath or with any unbonded metal shield	1334	300

**Note:** Cables with metallic sheaths that are evaluated and shown to protect the conductors to at least the same degree as an 175 µm (8 mil) aluminum bonded metal shield are acceptable over conductors having the lower crushing level. Interlocked steel or aluminum armour or corrugated or smooth continuous aluminum armour on a cable is acceptable protection for the conductors without test. Otherwise, the evaluation shall consist of a comparison of the performance of the other sheath with a bonded metal shield in the cable crushing and cable impact tests.

**Table 12  
Cold bend mandrel diameter  
(See Clause 7.5.)**

Diameter over insulated conductor mm (in)	Diameter of mandrel	
	mm	(in)
0 – 2.11 (0.083)	6.35	(0.250)
Over 2.11 (0.083) but not over 2.64 (0.104)	7.95	(0.313)
Over 2.64 (0.104) but not over 3.18 (0.125)	9.53	(0.375)
Over 3.18 (0.125) but not over 3.71 (0.146)	11.1	(0.438)
Over 3.71 (0.146) but not over 4.24 (0.167)	12.7	(0.500)
Over 4.24 (0.167) but not over 4.78 (0.188)	14.3	(0.563)
Over 4.78 (0.188) but not over 5.28 (0.208)	15.9	(0.625)

Table 12 Continued


Diameter over insulated conductor mm (in)	Diameter of mandrel	
	mm	(in)
Over 5.28 (0.208) but not over 5.82 (0.229)	17.5	(0.688)
Over 5.82 (0.229) but not over 6.35 (0.250)	19.1	(0.750)
Over 6.35 (0.250) but not over 6.88 (0.271)	20.7	(0.813)
Over 6.88 (0.271) but not over 7.42 (0.292)	22.2	(0.875)
Over 7.42 (0.292) but not over 8.46 (0.333)	25.4	(1.000)

**Table 13**  
**Cabling factor for calculating dc resistance**  
**(See Clause 7.16.3.)**

Construction	Multiplier
Cabled in one layer	1.02
Cabled in more than one layer	1.03
Cabled as one pair	1.04
Cabled as an assembly of pairs or other precabled units	1.04


**Note:** *Multipliers larger than the above shall be used when the manufacturer demonstrates that they are required.*

**Figure 1**  
**Integral flat cable**  
 (See Table 6.)

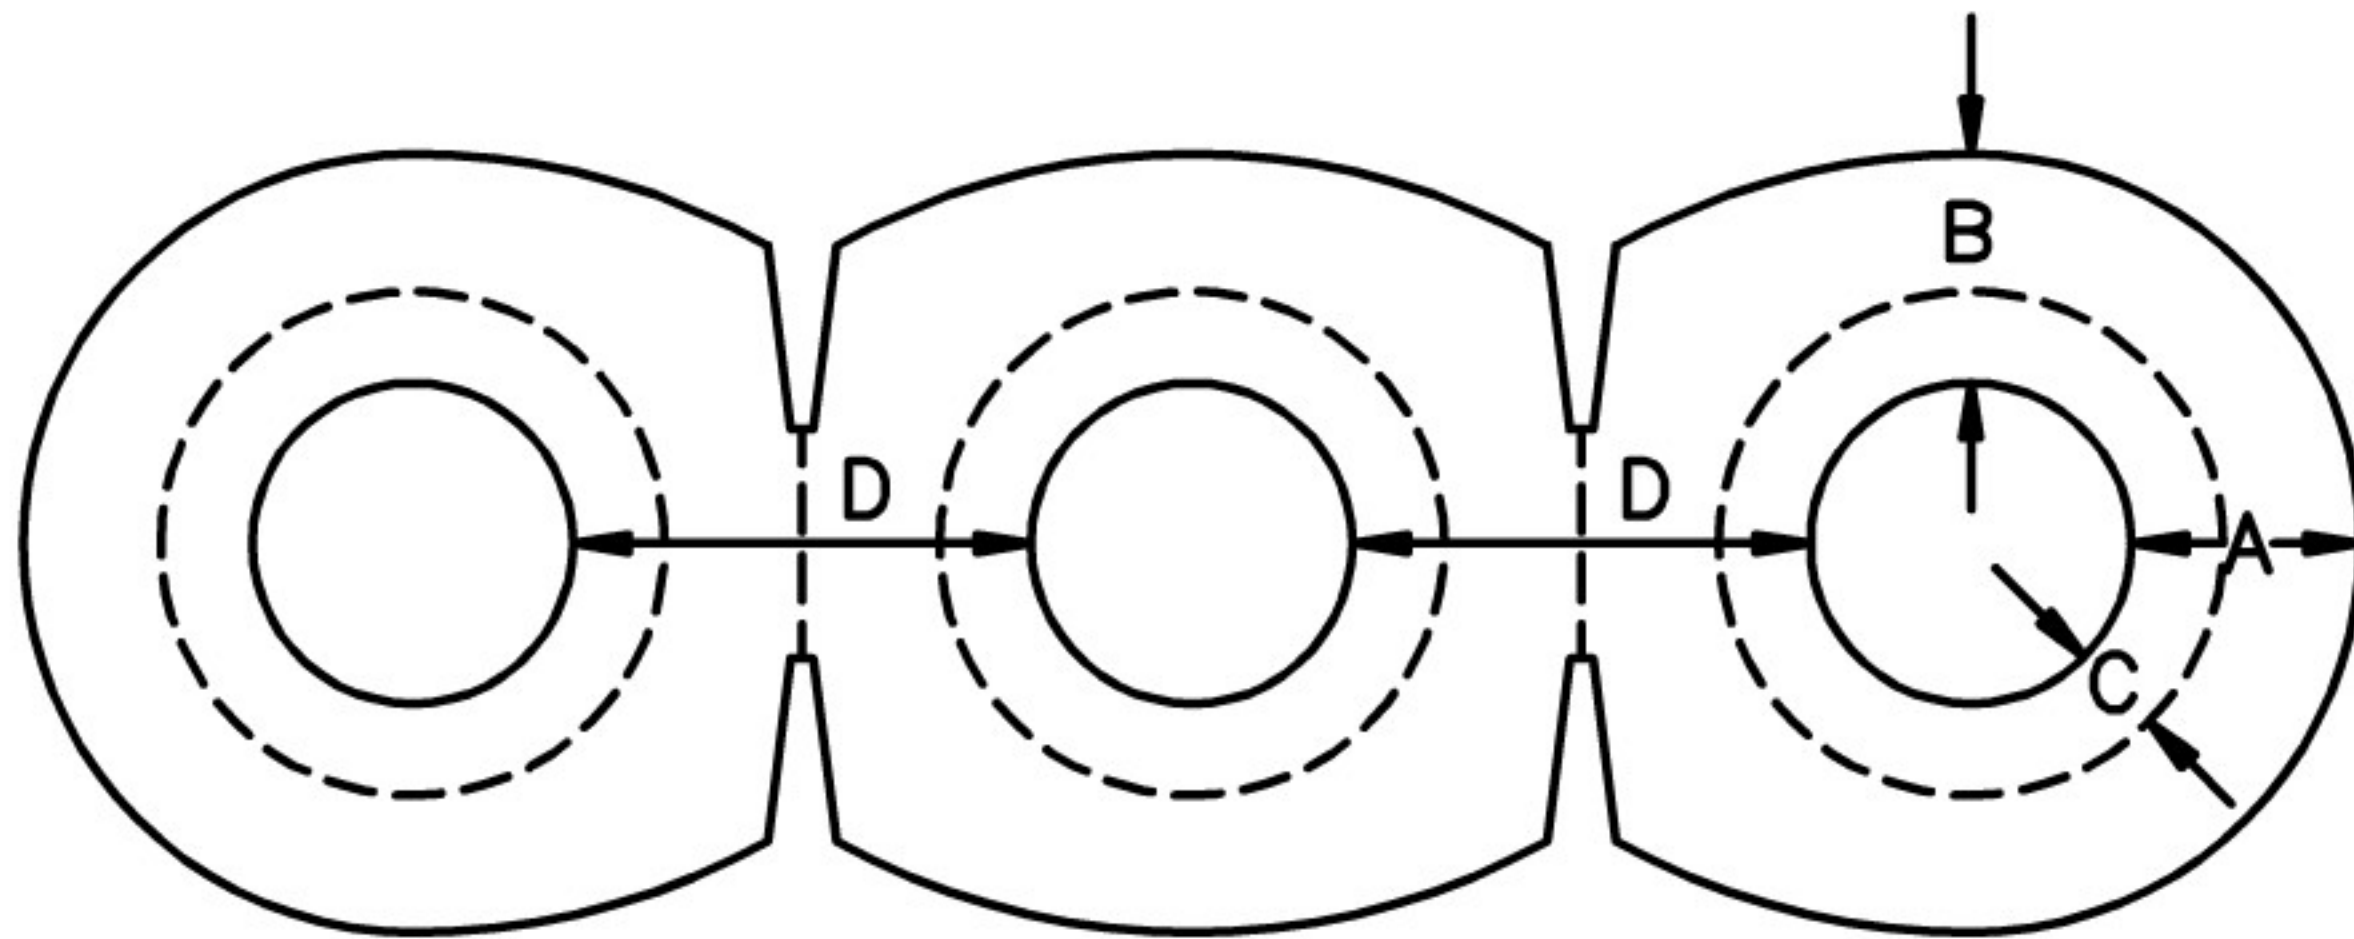

SB0636-2


**Figure 2**  
**Definition of regions of valley slopes on which thickness measurements are not to be made in integral flat cables**  
 (See Table 6.)

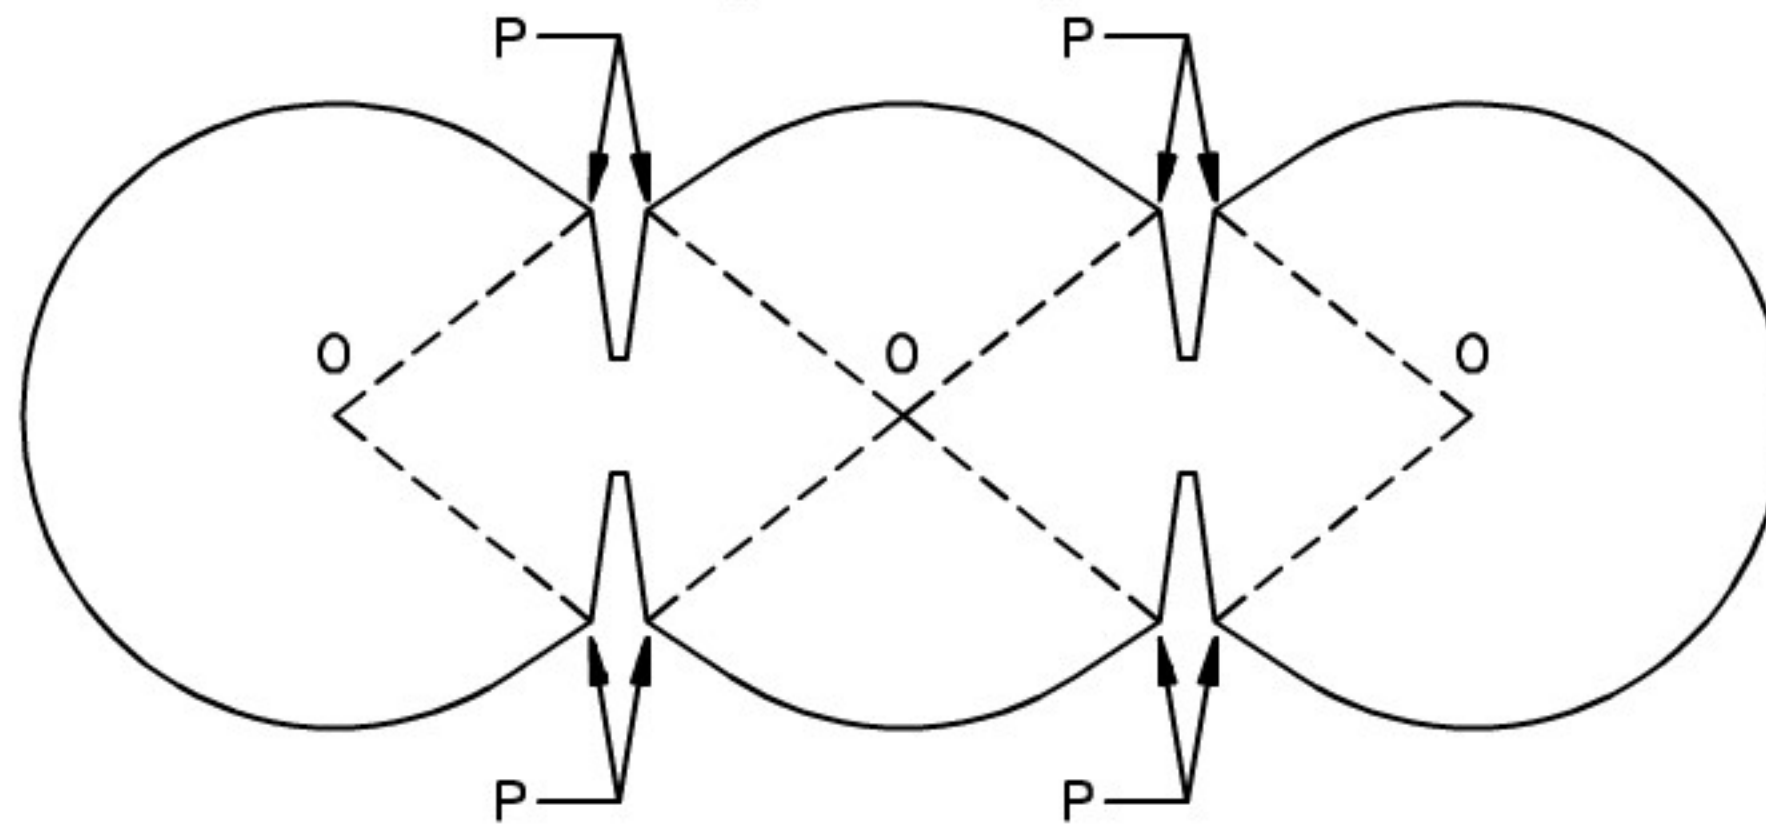

SB0636-5

**a) Constructions with a Cross-Section Having a Definite Point P at the Outer End of Each Valley**


Slope OP in each case is a straight line from the centre O of a conductor to P on the same segment of the cross-section. Thickness measurements are not to be made on any valley slope.

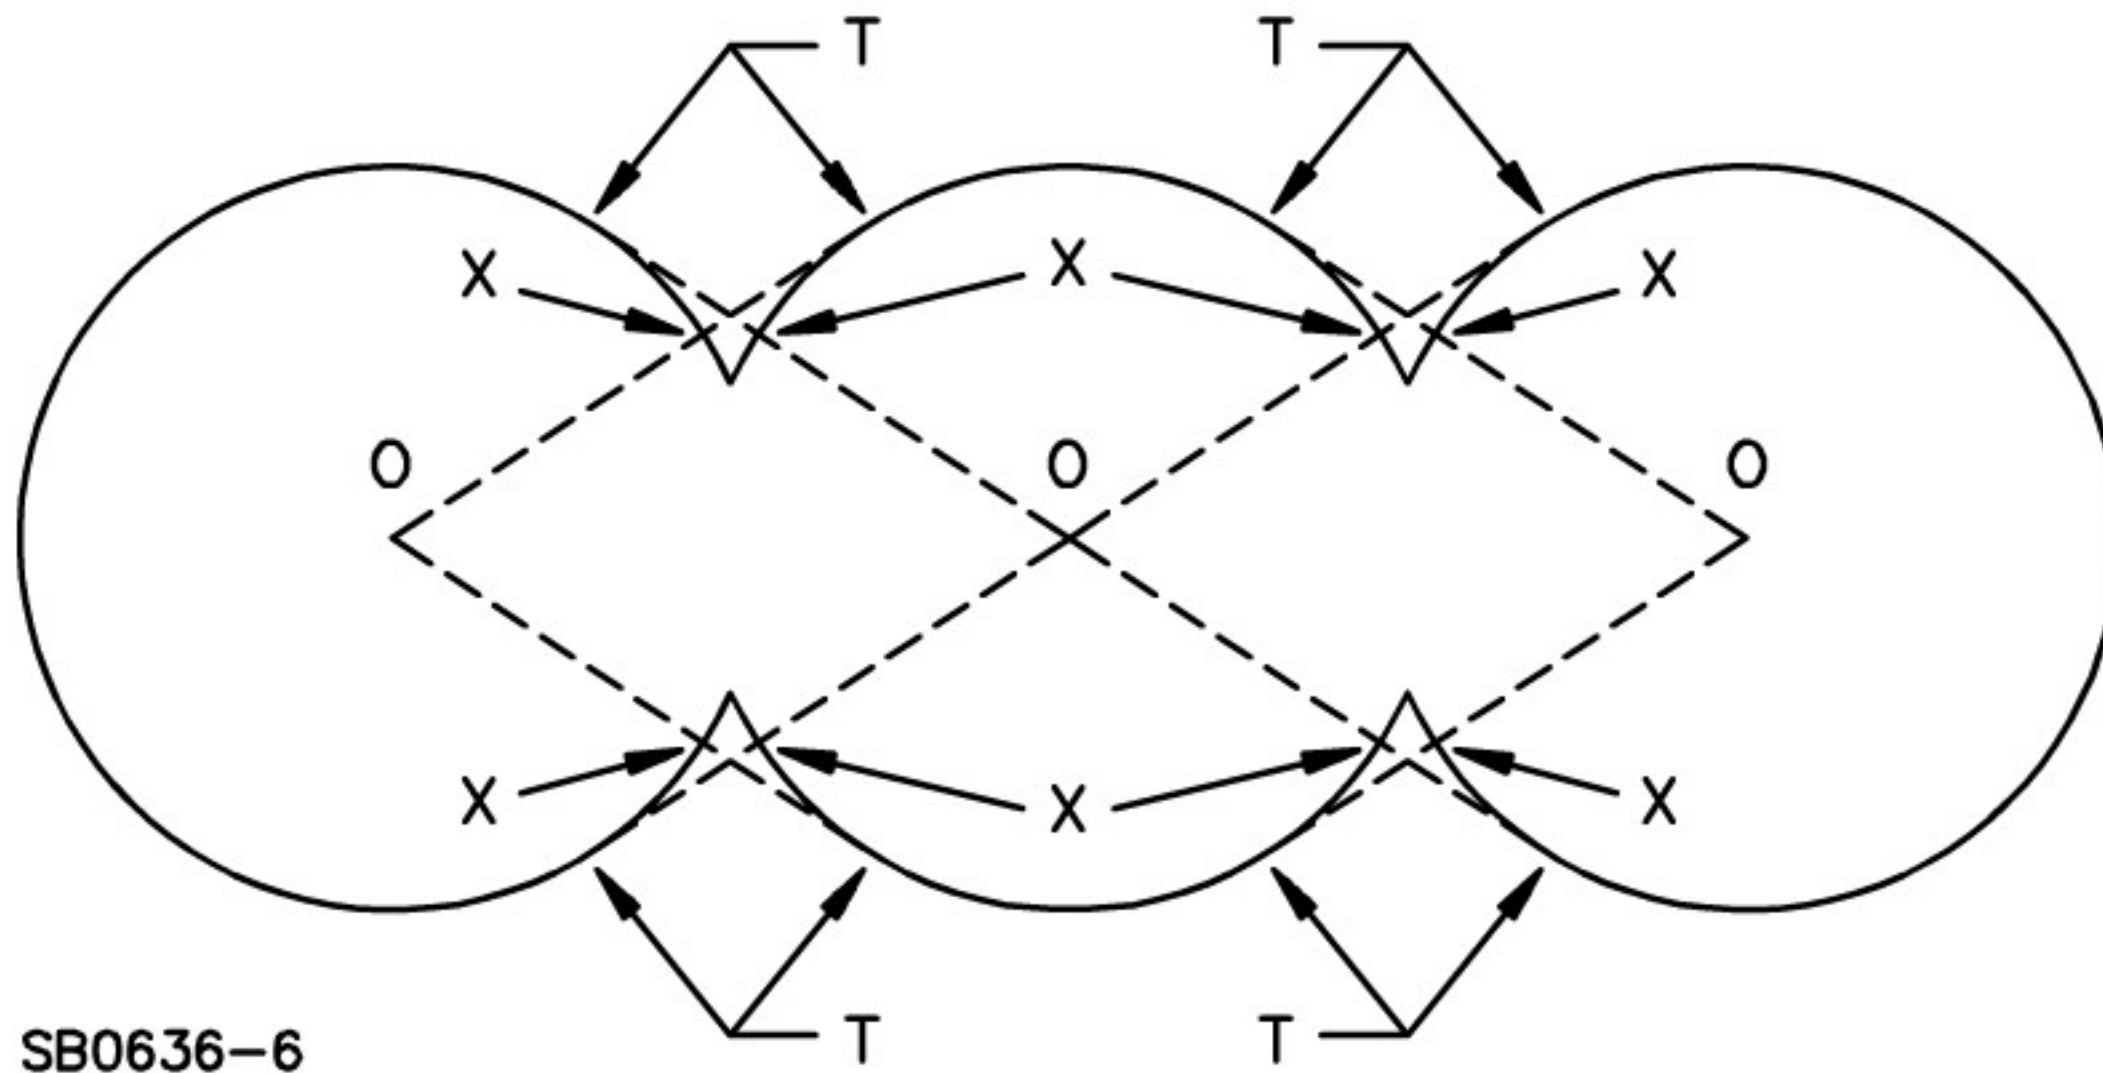

**b) Constructions with a Cross-Section not Having a Definite Point to Mark the Outer End of Each Valley**

Slope OT in each case is a straight line from the centre O of a conductor to T, the point of tangency, on the adjacent segment of the cross-section. Thickness measurements are not to be made deeper on a valley slope than point X, which is the intersection of the line OT with the valley slope. Thickness measurements are to be made on each slope segment TX.

**Figure 3**  
**Cold impact anvil**  
(See Clause 7.13.2.)

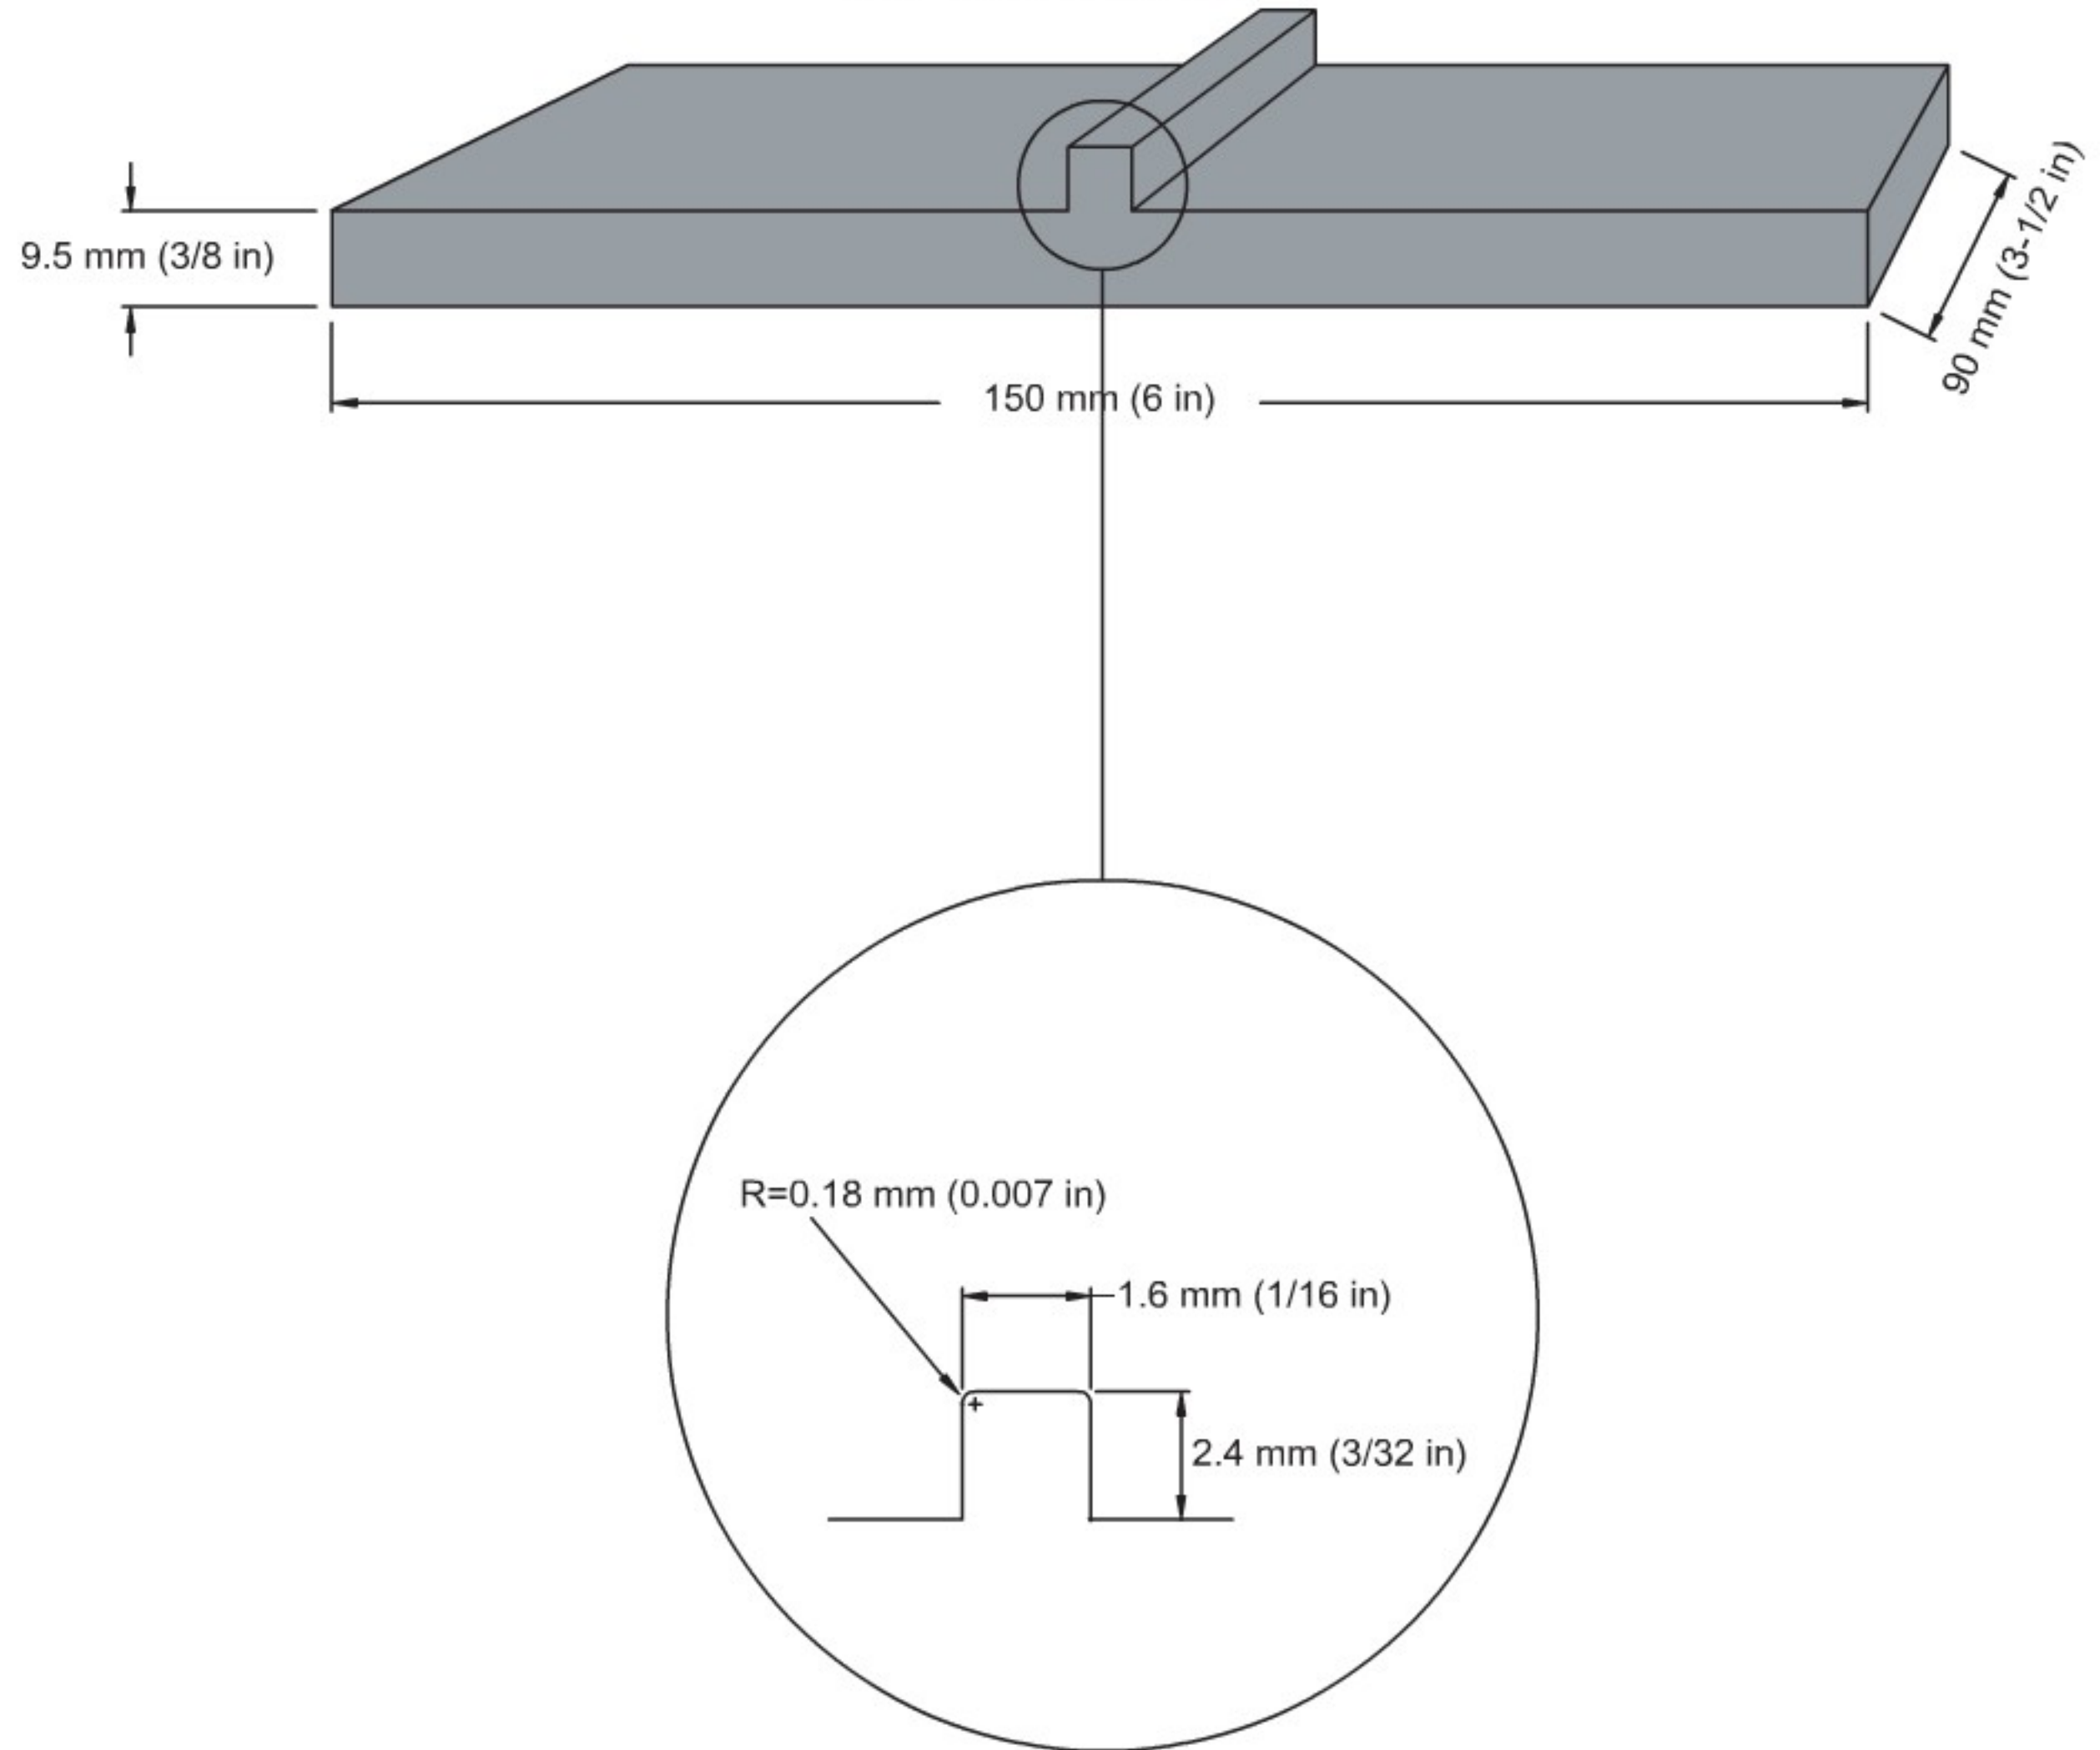

S5451

**ANNEX A****Electrical codes for wire types**

**Note:** *This Annex is an informative (nonmandatory) part of this standard.*

**Table A1**  
**Electrical codes for wire types**

<b>Wire type designation</b>	<b>Canada: Canadian Electrical Code, Part I</b>	<b>United States: National Electrical Code (NEC)</b>
CMP	YES	YES
CMR	YES	YES
CMG	YES	YES
CM	YES	YES
CMX	YES	YES
CMH	YES	NO
CMUC	YES	YES



**ANNEX B****Guidelines for sample selection for flame and smoke test requirements**

**Note:** *This Annex is an informative (nonmandatory) part of this standard.*

**Table B1**  
**Guidelines for sample selection for flame and smoke test requirements**

<b>Flame and smoke test</b>	<b>Sample selection</b>
FT1 or VW1	No guidelines needed
FT4 or UL flame exposure or FT4/IEEE 1202 Type of flame exposure in UL 1685 (without smoke measurements)	One set each of the smallest, largest, and intermediate diameters in the product range
UL 1666	Typically the test samples for these cables are the smallest diameter in the product range
CSA FT6, NFPA 262	Typically the test samples for these cables are the smallest and largest diameters in the product range

## ANNEX C

### Cable substitutions

**Note:** *This Annex is an informative (nonmandatory) part of this standard.*

C1 The following cable substitutions are appropriate:

- (a) Communications cables marked CMP, CMR, CMG, CM, CMX, CMH, FT6, FT4, or FT4/1202 have been found to meet the standard criteria for FT1.
- (b) Communications cables marked CMP, CMR, CMG, or FT6 have been found to meet the standard criteria for FT4 and FT4/1202.
- (c) Communications cables marked CMP have been found to meet the standard criteria for FT6.



333 Pfingsten Road  
Northbrook, Illinois 60062-2096  
847.272.8800

For other locations in the UL family of companies,  
please visit [UL.com/contact](http://UL.com/contact)